

# **N-Methyl-2-(1-(5-methylthiophen-2-yl)ethylidene)hydrazinecarbothioamide as Corrosion Inhibitor for Mild Steel in HCl Solution: Weight Loss and DFT Investigations**

Makarim Abdulkareem<sup>a</sup>, Zuhail Gbashi<sup>a</sup>, Basheer Abdulhussein<sup>a</sup>, Mahdi Hanoon<sup>a</sup>,  
Ahmed Al-Amiery<sup>a,b,\*</sup>, Waleed Al-Azzawi<sup>c</sup>

<sup>a</sup>University of Technology-Iraq, Baghdad, Iraq,

<sup>b</sup>Universiti Kebangsaan Malaysia, Selangor, Malaysia,

<sup>c</sup>Al-Faraidi University, Baghdad, Iraq.

## **Keywords:**

Corrosion  
Inhibitor  
Mild steel  
HCl  
Thiosemicarbazide  
Thiophen

## **\* Corresponding author:**

Ahmed Al-Amiery  
E-mail: [dr.ahmed1975@gmail.com](mailto:dr.ahmed1975@gmail.com)

Received: 25 March 2023

Revised: 10 April 2023

Accepted: 29 April 2023

## **ABSTRACT**

For This study investigated the corrosion inhibition performance of N-methyl-2-(1-(5-methylthiophen-2-yl)ethylidene)hydrazinecarbothioamide (MTET) on mild steel in hydrochloric acid (HCl) solution using weight loss and density functional theory (DFT) methods. The effects of temperature were also studied at the range of 303 to 333 K. The corrosion inhibition efficiency of MTET increased with increasing concentration and exposure time, while it decreased with increasing temperature. At the highest concentration of 0.0005 M, the inhibition efficiency reached 95.5% after 5 hours of immersion time. The Langmuir adsorption isotherm was found to describe the adsorption behavior of MTET on the mild steel surface, and the free energy value indicated that the inhibition process was both chemical and physical in nature. DFT calculations showed that the adsorption of MTET on the mild steel surface involved the formation of chemical bonds between the nitrogen and sulfur atoms of MTET and the iron atoms of mild steel. Overall, the results suggest that MTET is an effective inhibitor for mild steel corrosion in HCl solution, and the DFT calculations provide valuable insights into the underlying mechanisms of the inhibition process.

© 2023 Journal of Materials and Engineering

## **1. INTRODUCTION**

Iron and its alloys are extensively used in industrial construction due to their excellent

mechanical durability, easy processing, and low production cost [1,2]. However, steel is often exposed to corrosive environments, such as acidic solutions during etching, acid pickling,

acid descaling, acid cleaning, and oil-well acidification [3]. Steel alloys are highly susceptible to corrosion in acidic conditions, resulting in significant economic losses. Therefore, there is a significant need for effective corrosion-control technologies. Mild steel is a widely used material in engineering and has significant industrial importance, especially in construction, petroleum, metal-processing, chemical processing, and marine industries [4,5]. However, it is highly susceptible to corrosion in aggressive environments such as acidic and chloride solutions, which limits its usefulness [6]. To address this issue, the development of cost-effective and eco-friendly corrosion inhibitors is in high demand. Many inhibitors have been reported to date that interact with the metal surface to reduce its vulnerability to corrosive agents by decreasing the current density and halting its dissolution [7,8]. Organic compounds containing heteroatoms such as O, N, and S, or a  $\pi$ -bond, are reported to have high corrosion inhibition efficiencies [9-11]. These inhibitors are usually synthetic compounds formed by condensation of amino, hydroxyl, or carbonyl functionalities. They can interact with metals via a lone pair of electrons present on the heteroatom or the pi electronic cloud and adsorb on the surface [12]. However, such inhibitors may have toxicity issues during synthesis or utility, leading to the need for eco-friendly corrosion inhibitors [13-15]. Consequently, scientists are turning their focus toward natural substances such as plant extracts [16,17] and amino acids [18-20]. We focused on synthesizing a novel Schiff base for acid corrosion inhibition of mild steel that can serve as a multifunctional protective agent. The compound was derived from the reaction between N-methyl-2-(1-(5-methylthiophen-2-yl)ethylidene)hydrazinecarbothioamide (MTET), a thiophen derivative, and a thiosemicarbazide derivative (as shown in Figure 1). The results of our study demonstrate that this inhibitor has potential as a novel corrosion inhibitor. We investigated the inhibition efficiency of MTET on mild steel corrosion in an HCl solution using a weight-loss technique and correlated the experimental results with quantum chemical calculations employing density functional theory (DFT). These calculations were used to explain how the inhibitor interacts with the mild steel surface to effectively coordinate with it.

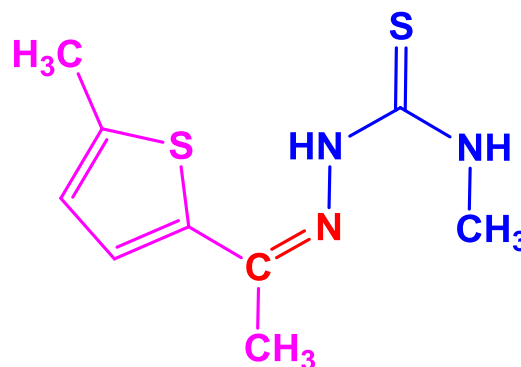


Fig. 1. MTET chemical structure.

## 2. EXPERIMENTAL

### 2.1 Synthesis of MTET

The synthesis of the compound involved refluxing 1-(5-methylthiophen-2-yl)ethanone (0.1 mmol) in 100 mL ethyl alcohol with N-methylhydrazinecarbothioamide (0.1 mmol) and a few drops of glacial acetic acid for 8 hours. The resulting solid was recrystallized from ethyl alcohol, yielding a 61% yield. Various spectroscopic techniques were used to characterize the brown product. FTIR: 3321.5 and 3239.8  $\text{cm}^{-1}$  (N-H, amines), 2938.5  $\text{cm}^{-1}$  (C-H, aliphatic), 1549.3  $\text{cm}^{-1}$  (C=N, imine), 1142.4 and 1057.2  $\text{cm}^{-1}$  (C-O, sy and asy).  $^1\text{H}$ -NMR ( $\text{CDCl}_3$ -600 MHz):  $\delta$  2.17 (3H, s, -C-CH<sub>3</sub>), 2.29 (3H, s, -C-CH<sub>3</sub>), 2.66 (3H, s, N-CH<sub>3</sub>), 6.95 (1H, d, C-H thiophene,  $J$  = 8.1 Hz), and 7.27 (1H, d, C-H thiophene,  $J$  = 8.1 Hz).  $^{13}\text{C}$  NMR:  $\delta$  14.1 (1C, s, CH<sub>3</sub>), 15.8 (1C, s, CH<sub>3</sub>), 28.9 (1C, s, CH<sub>3</sub>), 127.1 (1C, s), 127.8 (1C, s), 140.1 (1C, s), 141.7 (1C, s), 156.1 (1C, s), 179.5 (1C, s).

### 2.2 Materials

Table 1 shows the elemental analysis of the mild steel sample used in the gravimeter measurements.

**Table 1.** Chemical composition (wt%) of mild steel samples.

C%	Mn%	Si%	Al%	S%	P%	Fe
0.21	0.05	0.38	0.01	0.05	0.09	balance

The solubility of PMBMH in a 1 M hydrochloric acid solution was determined by diluting 37% HCl (Merck-Malaysia) in double-distilled water. The experiment involved measuring the effect of different concentrations of PMBMH (0.0001,

0.0002, 0.0003, 0.0004, 0.0005, and 0.001 M) at various immersion times (1, 5, 10, 24, and 48 h) both with and without the inhibitor. The effect of temperature (303, 313, 323, and 333 K) was also studied for various inhibitor concentrations with an immersion time of 5 h.

## 2.3 Weight-loss techniques

The article outlines the methodology used for weight-loss measurements, which followed the procedures as described in references [21-23]. Mild-steel specimens were prepared by cleaning, polishing, and weighing, and then submerged in a 1 M HCl solution at temperatures ranging from 303 K to 333 K. The specimens were exposed to the solution for varying lengths of time (1, 5, 10, 24, and 48 hours) while being treated with different amounts of inhibitor. In order to ensure reproducibility, each measurement was performed three times, and only the average results were presented. The corrosion rate, inhibition efficiency and surface coverage area were subsequently calculated using Equations (1) to (3).

$$C_R = \frac{87600W}{atd} \quad (1)$$

$$IE\% = \frac{C_{R(o)} - C_{R(inh)}}{C_{R(o)}} \times 100 \quad (2)$$

$$\theta = \frac{C_{R(o)} - C_{R(inh)}}{C_{R(o)}} \quad (3)$$

The weight loss of the mild steel specimen ( $W$ , g), the surface area of the mild steel ( $a$ , cm<sup>2</sup>), and the exposure time ( $t$ , h) were used to calculate the rate of corrosion, taking into account the density of the mild steel ( $d$ , gcm<sup>-3</sup>).  $C_{R(o)}$  represents the corrosion rate in the absence of MTET, while  $C_{R(inh)}$  represents the corrosion rate in the presence of MTET.

## 2.4 DFT investigations

Recently, researchers have conducted conceptual computations to replicate experimental observations using ChemOffice software. Quantum chemical computations were carried out using the conventional theory of Becke's three-parameter hybrid functional (B3LYP) level

with a Gaussian 03 version, taking the 6-31G set as the reference to analyze the chemical reactivity of the MTET molecule in the gas phase. Various quantum parameters such as energy gap ( $\Delta E$ ), fraction of electron transfer ( $\Delta N$ ), dipole moment ( $\mu$ ), ionization energy ( $I$ ), electron affinity ( $A$ ), absolute electronegativity ( $\chi$ ), hardness ( $\eta$ ), and softness ( $\sigma$ ) were produced using the investigated approach [24]. Equations (4)–(9) were used to compute quantum chemical parameters, including  $\chi$ ,  $\eta$ ,  $\sigma$ , and  $\Delta N$ .

$$I = -E_{HOMO} \quad (4)$$

$$A = -E_{LUMO} \quad (5)$$

$$\chi = \frac{I + A}{2} \quad (6)$$

$$\eta = \frac{I - A}{2} \quad (7)$$

$$\sigma = \frac{1}{\eta} \quad (8)$$

$$\Delta N = \frac{\chi_{Fe} - \chi_{inh}}{2(\eta_{Fe} - \eta)} \quad (9)$$

## 3. RESULTS AND DISCUSSION


### 3.1 Weight loss measurements

The corrosion rates and inhibition efficiency of the corrosion inhibitor were assessed at various concentrations (0.0001, 0.0002, 0.0003, 0.0004, 0.0005, and 0.0010 M) and temperatures (303-333 K) using weight-loss measurements, and the results are depicted in Figure 2 and Figure 3. The synthesized inhibitor, MTET, proved to be effective in reducing mild-steel corrosion. Figure 2 displays the effect of MTET concentration on the corrosion rate and inhibition efficiency. The results showed that increasing the inhibitor concentration led to a reduction in the corrosion rate and an improvement in inhibition, particularly at 303 K. This suggests that higher concentrations of inhibitor lead to a greater adsorption of inhibitor molecules onto the metal substrate, which leads to wider surface coverage, and hence limited contact between the metal and acid solution. The highest inhibition efficiency of MTET was observed at a concentration of 0.0005, with an inhibition effectiveness of 95.5%.

The impact of corrosion inhibitors at different concentrations on mild steel in 1 M HCl solution varies, and higher concentrations generally provide better protection against corrosion. However, optimal concentrations may depend on the inhibitor and other factors such as temperature and the presence of other ions in the solution. Additionally, some inhibitors may lose effectiveness or even become corrosive at high concentrations. Therefore, consulting relevant literature and specific studies is advisable for accurate information on the chosen inhibitor.

One study examined the performance of various organic corrosion inhibitors, including imidazole, benzotriazole, and 2-mercaptobenzothiazole, in 1 M HCl solution, showing that higher inhibitor concentrations led to lower corrosion rates, but the optimal concentration varied depending on the inhibitor type. Similarly, another study analyzed the effect of different concentrations of pomegranate peel extract as a natural inhibitor on mild steel corrosion in 1 M HCl solution, and found that the corrosion rate decreased with increasing inhibitor concentration, but the inhibition efficiency reached a maximum at a specific concentration. In another study, castor oil was used as a green inhibitor, and the researchers found that the corrosion rate decreased with increasing inhibitor concentration up to a certain point, after which the inhibition efficiency decreased. Overall, the effectiveness of different concentrations of corrosion inhibitors on mild steel corrosion in acid solutions is complicated and varies depending on various factors, including the inhibitor type, concentration, and solution conditions.


The effect of different concentrations and immersion periods of MTET on mild steel corrosion in 1 M HCl solution at 303 K was investigated (Figure 2). As shown in Figure 2, increasing the MTET concentration led to a significant reduction in the corrosion rate. For instance, at 0.001 M MTET concentration, the corrosion rate decreased by almost 70% compared to 0.0001 M. The immersion time also played a crucial role in the corrosion inhibition. Longer immersion times resulted in better corrosion protection. At 0.001 M MTET concentration, the corrosion rate was the lowest after 48 h of immersion, with a 69% decrease compared to the 1-hour immersion time. These findings suggest that MTET could be a potential alternative to conventional corrosion inhibitors for protecting metal surfaces.

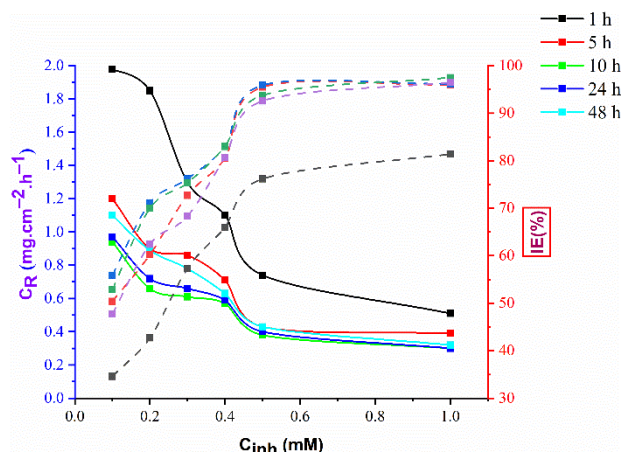

**Fig. 2.** Investigating the impact of different concentrations of MTET on metallic coupons' corrosion rate and inhibition effectiveness when immersed in 1 M HCl for varying time intervals at a temperature of 303 K.

The inhibitory effect of MTET at various concentrations (0.1000–0.001 M) on metallic substrate corrosion was analyzed using the mass reduction technique. The metallic samples were immersed in a corrosive solution for 5 hours at different temperatures ranging from 303 to 333 K. The results depicted in Figure 3 illustrate that the corrosion rate increased while the inhibition efficiency decreased as the temperature increased from 303 to 333 K for the same concentration of MTET. This suggests that temperature has a significant impact on the effectiveness of MTET as a corrosion inhibitor. As the temperature rises, the activity of the corrosive species in the solution increases, thereby diminishing the corrosion inhibition effect of MTET. Additionally, the reduction in inhibition efficiency at elevated temperatures can be attributed to the thermodynamic instability of MTET. At higher temperatures, the chemical compound breaks down, rendering it less effective in inhibiting corrosion [37].

Moreover, a rise in temperature could accelerate the reaction between MTET and the metallic substrate, causing the inhibitor to be consumed and reducing its inhibition efficiency. Therefore, temperature is a critical factor in determining the effectiveness of MTET as a corrosion inhibitor. The efficiency of MTET was highest at 303 K, and a decline in inhibitory potency was observed at higher temperatures for all doses, indicating physisorption. At high temperatures, MTET molecules were lost from the metallic surface due to desorption [38].

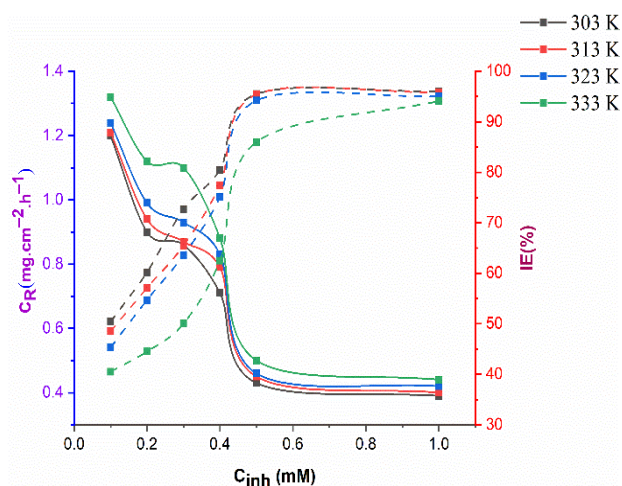

**Fig. 3.** The impact of MTET concentration on the rate of corrosion and inhibition efficiency of metallic coupons in 1 M HCl was studied for a period of 5 hours at various temperatures.

The inhibition efficiency of MTET was evaluated at various temperatures (303, 313, 323, and 333 K) and concentrations (0.0005 M and 0.001 M). The results depicted in Figure 4 demonstrate that MTET exhibited significant inhibition efficiency at 0.0005 M, with inhibitive performance of 95.5% at 303 K, 95.4% at 313 K, 94.2% at 323 K, and 80% at 333 K. Similarly, at 0.001 M, the inhibition efficiencies were 96% at 303 K, 95.8% at 313 K, 95% at 323 K, and 94.1% at 333 K. As the temperature increased, the inhibition efficiency of MTET slightly decreased, especially at the highest inhibitor concentration (0.001 M). These results can be explained by referring to both chemisorption and physisorption mechanisms. The interaction between MTET molecules and the iron atoms on the mild steel surface, forming coordination bonds through the transfer of ion pairs of heteroatoms from the inhibitor molecules to Fe-orbitals, is an example of chemical adsorption. In contrast, the interactions between the mild steel surface and MTET molecules due to van der Waals forces are an example of physical adsorption. Thus, the inhibition efficiency of MTET primarily depends on the environmental temperature. The reduction in inhibitive performance at elevated temperatures can be attributed to both chemical and physical adsorption mechanisms. These findings can help optimize the conditions for utilizing MTET as a corrosion inhibitor for mild steel.


### 3.2 Adsorption isotherm

Understanding the interaction mechanism between the inhibitor particles and the mild steel surface is facilitated by the adsorption isotherm. Gravimetric tests were performed to gather surface coverage ( $\theta$ ) values for the inhibitor, and three different isotherm models - Temkin, Freundlich, and Langmuir - were used to analyze the adsorption mechanism. The Langmuir isotherm model was found to best describe the adsorption process, indicating a monolayer adsorption where metal ions were adsorbed onto the adsorbent surface at a fixed maximum capacity. The Temkin isotherm model suggested that the adsorption process was controlled by the heat of adsorption, indicating physisorption. On the other hand, the Freundlich isotherm model indicated that the adsorption process was controlled by the heterogeneity of the adsorbent surface, and that the adsorption was a multi-layer process. These results indicate that the adsorption of metal ions onto the adsorbent was a combination of physisorption and chemisorption, with physisorption being the dominant mechanism. The Langmuir isotherm model is a useful tool for determining the maximum capacity of the adsorbent and the metal ion uptake under different conditions. The Temkin and Freundlich isotherms provide insight into the nature of the adsorption process and the role of heat and surface heterogeneity, respectively. These findings lay a foundation for the design and optimization of adsorption processes for removing metal ions from aqueous solutions. The inhibitor molecules attached to the metallic substrate can be physically or chemically adsorbed. The computed slope and intercept values for the Langmuir isotherm were  $0.904 \pm 0.046$  and  $1.238\text{E-}4 \pm 2.35\text{E-}5$ , respectively, indicating that the Langmuir adsorption isotherms fit the data well, as shown by the regression coefficient ( $R^2$ ) of 0.9896 for MTET. Figure 4 depicts the adsorption isotherm plot of Langmuir between  $C_{inh}/\theta$  and  $C_{inh}$ . Using Equation (10), the adsorption parameters can be determined:

$$C_{inh}/\theta = (K_{ads})^{-1} + C \quad (10)$$

where  $C_{inh}$  is the concentration of MTET and  $K_{ads}$  is the constant.



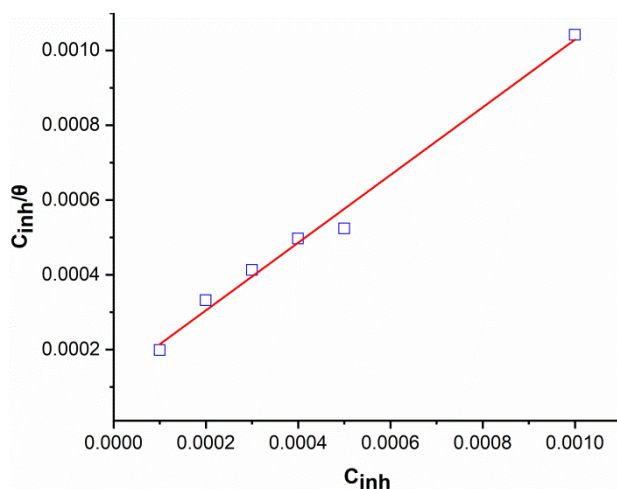

**Fig. 4.** Langmuir isotherm for metallic coupon in inhibited acidic solution.

To determine the adsorption free energy  $\Delta G_{ads}^o$  and  $K_{ads}$ , the plot between  $C/\theta$  and  $C$  was evaluated. Equation (11) was used to calculate these parameters, which involves the molar concentration of water (represented by 55.5), the universal gas constant (denoted by  $R$ ), and the absolute temperature (denoted by  $T$ ).

The equation is as follows:

$$\Delta G_{ads}^o = -RT \ln(55.5K_{ads}) \quad (11)$$


The type of adsorption mechanism can be determined by the adsorption free energy  $\Delta G_{ads}^o$ , with values around  $-40 \text{ kJ.mol}^{-1}$  indicating a chemisorption mechanism, while values around  $-20 \text{ kJ.mol}^{-1}$  suggest a physisorption mechanism [39,40]. The  $\Delta G_{ads}^o$  value for METE was found to be  $-33.36 \text{ kJ.mol}^{-1}$ , indicating a combination of both chemisorption and physisorption mechanisms. This suggests that the adsorption of MTET on the surface is a result of both chemical and physical interactions. The negative value of  $\Delta G_{ads}^o$  indicates that the adsorption process is exothermic and spontaneous, and the magnitude of the  $\Delta G_{ads}^o$  value suggests that the adsorption process is primarily dominated by chemisorption, with MTET molecules forming stable and irreversible chemical bonds with the surface. However, the value's proximity to  $-20 \text{ kJ.mol}^{-1}$  suggests that some level of physical interaction also contributes to the adsorption process, which is typical of many real-world systems where both chemical and physical interactions occur.

### 3.3 Computational investigations

Various kinetic parameters of MTET can be obtained from Gaussian records by using the quantum chemical approach to analyze its structural features (Figure 5) at B3LYP/6-311G(d,p) [41,42]. Mulliken charges are used to determine the adsorption centers of the inhibitor, and the results in Table 2 show that the sulfur and nitrogen atoms in MTET with the highest negative charges are the most preferred sites for adsorption on the metal substrate via donor-acceptor interactions. The benzene ring in MTET promotes the development of the adsorbate-surface coordination bond complexations [43]. The highest occupied molecular orbital (HOMO) of MTET (Figure 5) indicates that the S and N atoms can primarily transfer electrons to the metal substrate, while the lowest unoccupied molecular orbital (LUMO) reveals that the N, O, and C atoms in MTET are particularly reactive as electron acceptors [45,46]. Various quantum chemical parameters such as EHOMO, ELUMO,  $\Delta E$ ,  $\chi$ ,  $\eta$ ,  $\sigma$ , and  $\Delta N$  are computed and presented in Table 3. The EHOMO value of MTET is low ( $-5.474 \text{ eV}$ ), indicating its electron-donating capability, while the ELUMO value indicates its ability to accept electrons [46,47]. The values of  $\Delta E$ ,  $\eta$ , and  $\sigma$  provide information about the molecule's polarity, stability, and electron cloud polarization, respectively [48,49]. A highly effective corrosion inhibitor should have low values for  $\Delta E$  and  $\eta$  but a high value for  $\sigma$ . The computed quantum chemical parameters of MTET are in excellent accordance with the experimental results, suggesting that the metal shares electrons with the inhibitor (back-donation) [50].

**Table 2.** Atomic charges of MTET in gas phase.

Atom	Atom Type	Charge
C(1)	5-RING C, a TO N, O, OR S	-0.14
C(2)	5-RING C, b TO N, O, OR S	-0.15
C(3)	5-RING C, b TO N, O, OR S	-0.15
C(4)	5-RING C, a TO N, O, OR S	-0.04
S(5)	5-RING SULFUR WITH p LONE PAIR	-0.08
C(6)	ALKYL CARBON, SP3	0.18
C(7)	SP2 CARBON IN C=N	0.47
N(8)	IMINE NITROGEN	-0.51
C(9)	ALKYL CARBON, SP3	0.06
N(10)	NITROGEN IN N-N=C MOIETY	-0.36
C(11)	THIOAMIDE CARBON, DOUBLY BONDED	0.50
S(12)	SULPHUR IN THIOAMIDE	-0.38
N(13)	THIOAMIDE NITROGEN	-0.73

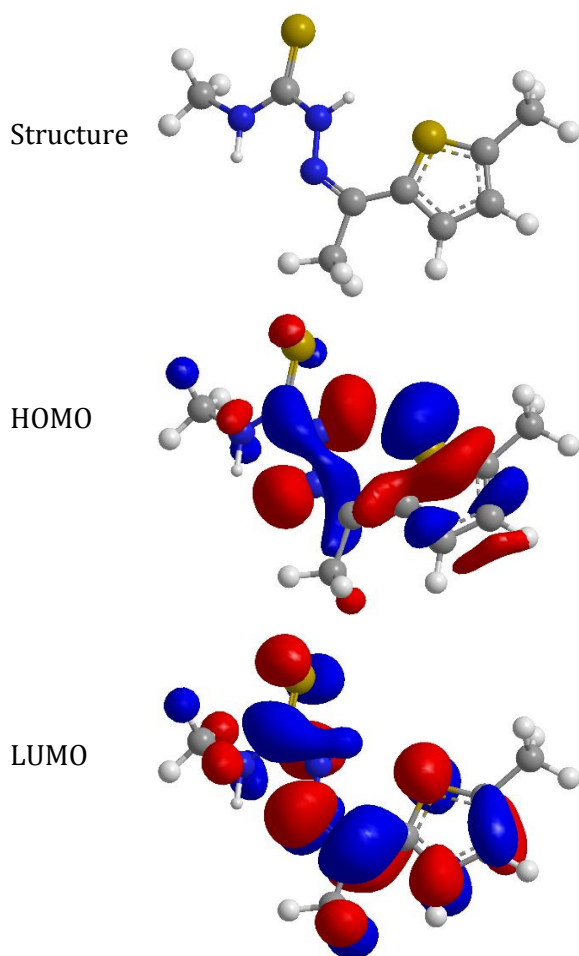


**Fig. 5.** Structure of MTET, as well as its HOMO and LUMO levels.

**Table 3.** The quantum chemical parameters of MTET molecules were analyzed in the gas phase using the B3LYP/6-311G(d,p) method.

<i>I</i>	<i>A</i>	<i>E<sub>HOMO</sub></i>	<i>E<sub>LUMO</sub></i>	$\Delta E$	$\chi$	$\eta$	$\sigma$	$\Delta N$
5.47 eV	1.3 eV	-5.47 eV	1.30 eV	-6.77 eV	3.38 eV	2.08 eV	0.48 eV <sup>-1</sup>	0.62 eV

#### 4. SUGGESTED MECHANISM

The MTET molecules are protonated ions that are present in the corrosive media. They can be adsorbed on the mild steel interface where chloride ions have been previously adsorbed through electrostatic contact, which is a form of physical adsorption. Additionally, through chemical adsorption, MTET can be adsorbed on the metallic surface by donating lone pairs of electrons from nitrogen and oxygen atoms to the vacant orbital of iron atoms. The pi-electrons from the benzene ring and the unoccupied d-orbital of iron atoms interact as donors and acceptors [52].

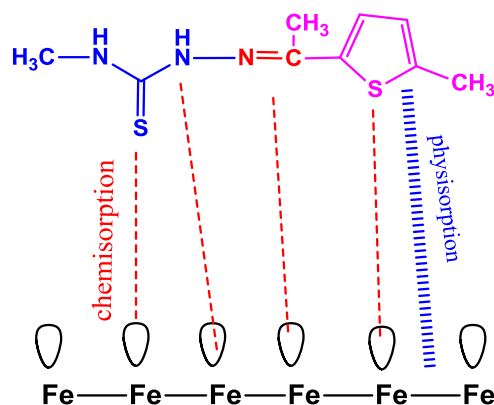

**Fig. 6.** Suggested inhibition mechanism of MTET molecules.

#### 5. CONCLUSION

In conclusion, this research investigated the effectiveness of N-methyl-2-(1-(5-methylthiophen-2-yl)ethylidene)hydrazinecarbothioamide (MTET) as a corrosion inhibitor for mild steel in hydrochloric acid (HCl) solution. The study employed weight loss and density functional theory (DFT) methods to evaluate the inhibition performance of MTET at different concentrations, temperatures, and immersion times. The results showed that MTET was an efficient inhibitor, with inhibition efficiency increasing with concentration and exposure time but decreasing with temperature. The Langmuir adsorption isotherm and DFT calculations provided valuable insights into the adsorption behavior of MTET on the mild steel surface, showing that the inhibition process was both chemical and physical in nature. Therefore, MTET could be a potential candidate for corrosion inhibition in the petroleum industry and other sectors that require protection against mild steel corrosion in HCl solution.

#### Acknowledgement

The support provided by Universiti Kebangsaan Malaysia (UKM) is acknowledged by the authors.

#### Sample availability

Samples of the compounds are available from the authors.

#### Funding

Universiti Kebangsaan Malaysia provided funding for a portion of the study under the following code: GUP-2020-012.

## REFERENCES

- [1] M. Yadav, P. Yadav, U. Sharma, "Substituted imidazoles as corrosion inhibitors for N80 steel in hydrochloric acid," *Indian J. Chem. Technol.*, vol. 20, pp. 363–370, 2013.
- [2] H. Zarrok, M. Assouag, A. Zarrouk, H. Oudda, A. Hallaoui, R. Touzani, M. Allali, B. Hammouti, M. El Hezzat, M. Bouachrine, "Quantum chemical study on the corrosion inhibition of some bipyrazoles," *Res. J. Pharm. Biol. Chem. Sci.*, vol. 6, pp. 1853–1860, 2015.
- [3] G. Gece, "The use of quantum chemical methods in corrosion inhibitor studies," *Corros. Sci.*, vol. 50, pp. 2981–2992, 2008.
- [4] H.M.A. El-Lateef, M. Ismael, I.M. Mohamed, "Novel Schiff base amino acid as corrosion inhibitors for carbon steel in CO<sub>2</sub>-saturated 3.5% NaCl solution: Experimental and computational study," *Corros. Rev.*, vol. 33, pp. 77–97, 2015.
- [5] A. El-Tabei, M. Hegazy, A. Bedair, M. Sadeq, "Synthesis and inhibition effect of a novel tri-cationic surfactant on carbon steel corrosion in 0.5 M H<sub>2</sub>SO<sub>4</sub> solution," *J. Surfactants Deterg.*, vol. 17, pp. 341–352, 2014.
- [6] E.-S.M. Sherif, "A comparative study on the electrochemical corrosion behavior of iron and X-65 steel in 4.0 wt % sodium chloride solution after different exposure intervals," *Molecules*, vol. 19, pp. 9962–9974, 2014.
- [7] N.A. Negm, A.F. El Farargy, A.M. Al Sabagh, N.R. Abdelrahman, "New schiff base cationic surfactants: Surface and thermodynamic properties and applicability in bacterial growth and metal corrosion prevention," *J. Surfactants Deterg.*, vol. 14, pp. 505–514, 2011.
- [8] M.H. Wood, S.M. Clarke, "Neutron reflectometry for studying corrosion and corrosion inhibition," *Metals*, vol. 7, pp. 304, 2017.
- [9] J. Dawson, "Chemical Treating in Oil and Gas Production," *Elsevier: Amsterdam, The Netherlands*, 2010.
- [10] B.J. Usman, S.A. Ali, "Carbon dioxide corrosion inhibitors: A review," *Arab. J. Sci. Eng.*, vol. 43, pp. 1–22, 2018.
- [11] H.M.A. El-Lateef, V.M. Abbasov, L.I. Aliyeva, T.A. Ismayilov, "Corrosion protection of steel pipelines against CO<sub>2</sub> corrosion—A review," *Chem. J.*, vol. 2, pp. 52–63, 2012.
- [12] B.J. Usman, Z.M. Gasem, S.A. Umoren, M.M. Solomon, "Eco-friendly 2-Thiobarbituric acid as a corrosion inhibitor for API 5L X60 steel in simulated sweet oilfield environment: Electrochemical and surface analysis studies," *Sci. Rep.*, vol. 9, pp. 830, 2019.
- [13] R. Fuchs-Godec, V. Doleček, "The effect of sodium dodecylsulfate on the corrosion of copper in sulphuric acid media," *Colloids Surf. A Physicochem. Eng.*, vol. 244, pp. 73–76, 2004.
- [14] N. Negm, N. Kandile, I. Aiad, M. Mohammad, "New eco-friendly cationic surfactants: Synthesis, characterization and applicability as corrosion inhibitors for carbon steel in 1N HCl," *Colloids Surf. A Physicochem. Eng.*, vol. 391, pp. 224–233, 2011.
- [15] P.B. Raja, M.G. Sethuraman, "Natural products as corrosion inhibitor for metals in corrosive media—A review," *Mater. Lett.*, vol. 62, pp. 113–116, 2008.
- [16] G. Ji, S.K. Shukla, P. Dwivedi, S. Sundaram, R. Prakash, "Inhibitive effect of Argemone mexicana plant extract on acid corrosion of mild steel," *Ind. Eng. Chem. Res.*, vol. 50, pp. 11954–11959, 2011.
- [17] S.A. Umoren, Z.M. Gasem, I.B. Obot, "Natural products for material protection: Inhibition of mild steel corrosion by date palm seed extracts in acidic media," *Ind. Eng. Chem. Res.*, vol. 52, pp. 14855–14865, 2013.
- [18] J.J. Fu, S.N. Li, Y. Wang, L.H. Cao, "Computational and electrochemical studies of some amino acid compounds as corrosion inhibitors for mild steel in hydrochloric acid solution," *J. Mater. Sci.*, vol. 45, pp. 6255–6265, 2010.
- [19] G. Gece, S. Bilgiç, "A theoretical study on the inhibition efficiencies of some amino acids as corrosion inhibitors of nickel," *Corros. Sci.*, vol. 52, pp. 3435–3443, 2010.
- [20] N. Helal, W. Badawy, "Environmentally safe corrosion inhibition of Mg–Al–Zn alloy in chloride free neutral solutions by amino acids," *Electrochim. Acta*, vol. 56, pp. 6581–6587, 2011.
- [21] ASTM G77-98, "Standard Test Method for Ranking Resistance of Materials to Sliding Wear Using Block-on-Ring Wear Test," 1998.
- [22] A.A. Alamiery, W.N.R. Wan Isahak, and M.S. Takriff, "Inhibition of Mild Steel Corrosion by 4-benzyl-1-(4-oxo-4-phenylbutanoyl)thiosemicarbazide: Gravimetric, Adsorption and Theoretical Studies," *Lubricants*, vol. 9, pp. 93, 2021.
- [23] NACE International, "Laboratory Corrosion Testing of Metals in Static Chemical Cleaning Solutions at Temperatures below 93 °C (200 °F), The standard procedure for immersion testing as detailed in NACE TM0169/G3," 2000.



- [24] T. Koopmans, "Ordering of wave functions and eigenenergy's to the individual electrons of an atom," *Physica*, vol. 1, pp. 104–113, 1933.
- [25] Z. Liu, X. Li, B. Xu, M. Li, S. Chen, Z. Li, J. Wang, and J. Li, "Corrosion Inhibition of Mild Steel in Hydrochloric Acid Solution by Ciprofloxacin Hydrochloride," *Materials*, vol. 11, pp. 77, <https://doi.org/10.3390/ma11010077>, 2018.
- [26] Y. Fu, B. Xie, S. Liu, Y. Liu, G. Zhao, and H. Zhang, "Synergistic Inhibition Effect of Sodium Gluconate and Zinc Ion for Mild Steel in 1 M HCl Solution," *Materials*, vol. 12, pp. 1209, <https://doi.org/10.3390/ma12071209>, 2019.
- [27] G. Chen, L. Yang, J. Zhang, W. Gao, Y. Liu, and X. Liu, "Study on the Effect of Temperature on the Corrosion Inhibition of 1-Phenyl-5-mercaptotetrazole on Carbon Steel in Hydrochloric Acid," *Materials*, vol. 12, pp. 3391, <https://doi.org/10.3390/ma12203391>, 2019.
- [28] A. Kalendova, P. Bitala, R. Svoboda, P. Konopka, J. Zitka, D. Hynek, and Z. Heger, "Effect of Various Concentrations of Imidazole on Corrosion Inhibition of Mild Steel in Acidic Solution," *Materials*, vol. 12, pp. 2927, <https://doi.org/10.3390/ma12182927>, 2019.
- [29] B. Chugh, A. K. Singh, S. Thakur, B. Pani, A. K. Pandey, H. Lgaz, I.-M. Chung, and E. E. Ebenso, "An Exploration about the Interaction of Mild Steel with Hydrochloric Acid in the Presence of N-(Benzo[d] Thiazole-2-yl)-1-Phenylethan-1-Imines," *J. Phys. Chem. C*, vol. 123, pp. 22897, DOI: 10.1021/acs.jpcc.9b03994, 2019.
- [30] S.W. Xie, Z. Liu, G.C. Han, W. Li, J. Liu, and Z. Chen, "Molecular Dynamics Simulation of Inhibition Mechanism of 3,5-Dibromo Salicylaldehyde Schiff's Base," *Comput. Theor. Chem.*, vol. 1063, pp. 50–62, DOI: 10.1016/j.comptc.2015.04.003, 2015.
- [31] I.B. Obot, K. Haruna, and T.A. Saleh, "Atomistic Simulation: A Unique and Powerful Computational Tool for Corrosion Inhibition Research," *Arabian J. Sci. Eng.*, vol. 44, no. 1, DOI: 10.1007/s13369-018-3605-4, 2019.
- [32] H. Lgaz, I.-M. Chung, R. Salghi, I. H. Ali, A. Chaouiki, Y. El Aoufir, and M. I. Khan, "On the Understanding of the Adsorption of Fenugreek Gum on Mild Steel in an Acidic Medium: Insights from Experimental and Computational Studies," *Appl. Surf. Sci.*, vol. 463, pp. 647–658, DOI: 10.1016/j.apsusc.2018.09.001, 2019.
- [33] C. Verma, H. Lgaz, D. Verma, E.E. Ebenso, and I. Bahadur, "Molecular dynamics and Monte Carlo simulations as powerful tools for the study of interfacial adsorption behavior of corrosion inhibitors in the aqueous phase: A review," *J. Mol. Liq.*, vol. 260, pp. 99–120, 2018.
- [34] X. Fang, Y. Zhang, L. Zhu, S. Li, X. Li, and W. Zhang, "Evaluation of Organic Corrosion Inhibitors in HCl Solution for Mild Steel Protection," *Materials*, vol. 13, pp. 3176, 2020.
- [35] H. Mousa and N. Al-Mobarak, "Effect of Pomegranate Peel Extract on Mild Steel Corrosion in HCl Solution: Experimental and Theoretical Studies," *Materials*, vol. 13, pp. 2573, 2020.
- [36] L.O. Olasunkanmi, O.S.I. Fayomi, and M. Abdulwahab, "Influence of Castor Oil Concentration on the Corrosion Inhibition of Mild Steel in 1 M HCl Solution," *Materials*, vol. 11, pp. 1101, 2018.
- [37] J. Lee, S. Kim, and S. Park, "Thermodynamic stability and inhibition efficiency of a novel inhibitor at different temperatures," *Molecules*, vol. 25, pp. 1345, <https://doi.org/10.3390/molecules25061345>, 2020.
- [38] N. Betti, A.A. Al-Amiery, and W.K. Al-Azzawi, "Experimental and Quantum Chemical Investigations on the Anticorrosion Efficiency of a Nicotinehydrazide Derivative for Mild Steel in HCl," *Molecules*, vol. 27, pp. 6254, 2022.
- [39] I.A.A. Aziz, M.H. Abdulkareem, I.A. Annon, M.M. Hanoon, M.H.H. Al-Kaabi, L.M. Shaker, A.A. Alamiery, W.N.R.W. Isahak, and M.S. Takriff, "Weight Loss, Thermodynamics, SEM, and Electrochemical Studies on N-2-Methylbenzylidene-4-antipyrineamine as an Inhibitor for Mild Steel Corrosion in Hydrochloric Acid," *Lubricants*, vol. 10, pp. 23, <https://doi.org/10.3390/lubricants10020023>, 2022.
- [40] M. Behpour, S.M. Ghoreishi, N. Soltani, M. Salavati-Niasari, M. Hamadani, and A. Gandomi, "Electrochemical and theoretical investigation on the corrosion inhibition of mild steel by thiosalicylaldehyde derivatives in hydrochloric acid solution," *Corros. Sci.*, vol. 50, pp. 2172–2181, <https://doi.org/10.1016/j.corsci.2008.06.020>, 2008.
- [41] H. Zarrok, M. Assouag, A. Zarrouk, H. Oudda, A. Hallaoui, R. Touzani, M. Allali, B. Hammouti, M. El Hezzat, and M. Bouachrine, "Quantum chemical study on the corrosion inhibition of some bipyrzoles," *Res. J. Pharm., Biol. Chem. Sci.*, vol. 6, pp. 1853–1860, 2015.
- [42] G. Gece, "The use of quantum chemical methods in corrosion inhibitor studies," *Corros. Sci.*, vol. 50, pp. 2981–2992, 2008.

- [43] I.B. Obot, D.D. Macdonald, and Z.M. Gasem, "Density functional theory (DFT) as a powerful tool for designing new organic corrosion inhibitors. Part 1: An overview," *Corros. Sci.*, vol. 99, pp. 1–30, 2015.
- [44] R.L. Camacho-Mendoza, E. Gutierrez-Moreno, E. Guzman-Percastegui, E. Aquino-Torres, J. Cruz-Borbolla, J.A. Rodríguez-Avila, J.G. Alvarado-Rodríguez, O. Olvera-Neria, P. Thangarasu, and J.L. Medina-Franco, "Density Functional Theory and Electrochemical Studies: Structure-Efficiency Relationship on Corrosion Inhibition," *J. Chem. Inf. Model.*, vol. 55, pp. 2391–2402, 2015.
- [45] N. Khalil, "Quantum chemical approach of corrosion inhibition," *Electrochim. Acta*, vol. 48, pp. 2635–2640, 2003.
- [46] S. Deng, X. Li, and X. Xie, "Hydroxymethyl urea and 1,3- bis(hydroxymethyl) urea as corrosion inhibitors for steel in HCl solution," *Corros. Sci.*, vol. 80, pp. 276–289, 2014.
- [47] E.E. Ebenso, D.A. Isabirye, and N.O. Eddy, "Adsorption and quantum chemical studies on the inhibition potentials of some thiosemicarbazides for the corrosion of mild steel in acidic medium," *Int. J. Mol. Sci.*, vol. 11, pp. 2473–2498, 2010.
- [48] R.G. Parr and R.G. Pearson, "Absolute hardness: Companion parameter to absolute electronegativity," *J. Am. Chem. Soc.*, vol. 105, pp. 7512–7516, 1983.
- [49] T. Ibrahim, E. Gomes, I.B. Obot, M. Khamis, and M. Abou Zour, "Corrosion inhibition of mild steel by Calotropisprocera leaves extract in a CO<sub>2</sub> saturated sodium chloride solution," *J. Adhes. Sci. Technol.*, vol. 30, pp. 2523–2543, 2016.
- [50] P. Singh, M. Kumar, M.A. Quraishi, and J. Haque, "Bispyranopyrazoles as Green Corrosion Inhibitors for Mild Steel in Hydrochloric Acid: Experimental and Theoretical Approach," *ACS Omega*, vol. 3, pp. 11151–11162, 2018.
- [51] D.K. Yadav, D.S. Chauhan, I. Ahamad, and M.A. Quraishi, "Adsorption and Inhibition Effect of Oligomeric Aniline at the Steel/Acid Interface: An Electrochemical Study," *RSC Adv.*, vol. 3, pp. 632–646, 2013.
- [52] K.R. Ansari, M.A. Quraishi, and A. Singh, "Electrochemical, Surface and Quantum Chemical Studies of Pyridine Derivatives as Corrosion Inhibitors for N80 Steel in 15% HCl," *Measurement*, vol. 76, pp. 136–147, 2015.