

## Schiff Bases as Corrosion Inhibitors: A Mini-Review

Ahmed A. Alamiery<sup>a,b\*</sup>

<sup>a</sup>Department of Chemical and Process Engineering, Faculty of Engineering and Built Environment, Universiti Kebangsaan Malaysia (UKM), Bangi 43000, Malaysia,

<sup>b</sup>Energy and Renewable Energies Technology Center, University of Technology, Iraq, 10001, Iraq.

### Keywords:

Schiff bases  
Corrosion inhibitors  
Metal corrosion  
Synthesis methods  
Surface protection

\* Corresponding author:

Ahmed A. Alamiery   
E-mail: [dr.ahmed1975@gmail.com](mailto:dr.ahmed1975@gmail.com)

Received: 29 November 2023

Revised: 20 December 2024

Accepted: 25 January 2024



### ABSTRACT

Corrosion, a ubiquitous and economically burdensome phenomenon, poses a persistent challenge across various industries. As the search for effective corrosion inhibitors intensifies, Schiff bases have emerged as promising candidates due to their versatile chemical structures and unique reactivity. This mini-review provides a comprehensive overview of the role of Schiff bases in corrosion inhibition. Beginning with an introduction to corrosion and the imperative for corrosion inhibitors, the paper delves into the structural features and synthesis methods of Schiff bases. The mechanism of corrosion inhibition by Schiff bases is elucidated, emphasizing their interactions with metal surfaces. Recent advances in the field are highlighted, shedding light on novel Schiff base modifications that exhibit enhanced corrosion inhibition efficiency. The review also addresses characterization techniques employed to study the interaction between Schiff bases and metal surfaces. Furthermore, the practical applications of Schiff bases as corrosion inhibitors in diverse industries are explored, taking into account their compatibility with various metals and environments. Despite the promising prospects, challenges and limitations associated with Schiff bases as corrosion inhibitors are discussed, providing insights into future research directions. In conclusion, this mini-review consolidates current knowledge, offering a succinct yet comprehensive overview of Schiff bases as effective corrosion inhibitors and outlining avenues for further exploration in this dynamic field.

© 2024 Journal of Materials and Engineering

### 1. INTRODUCTION


Corrosion, the gradual deterioration of metals due to environmental factors, is a pervasive issue affecting numerous industries worldwide. The economic and environmental repercussions of corrosion necessitate effective

strategies to mitigate its impact, and one promising avenue of exploration is the use of corrosion inhibitors. This section will provide a comprehensive introduction to the broader context of corrosion, setting the stage for the exploration of Schiff bases as corrosion inhibitors [1-5]. Corrosion is a natural

electrochemical process that leads to the gradual deterioration of metals, alloys, and other materials due to interactions with their environment (Figure 1). It involves the oxidation of metals, often facilitated by exposure to moisture, oxygen, acids, or other corrosive substances. This process can result in the formation of rust, tarnish, or other undesirable compounds on the surface of metals, compromising their structural integrity and functionality. The economic and environmental consequences of corrosion are profound and impact a multitude of industries. In economic terms, the cost of corrosion-related damages and maintenance is staggering. According to studies, corrosion is estimated to cost trillions of dollars globally each year, accounting for a significant percentage of a country's Gross Domestic Product (GDP). These costs encompass not only direct expenses for repairs and replacements but also indirect costs associated with downtime, loss of productivity, and compromised safety. In the infrastructure sector, corrosion poses a significant threat to the stability and longevity of bridges, pipelines, and buildings. For instance, steel-reinforced concrete structures are vulnerable to corrosion, especially in coastal regions where exposure to saltwater accelerates the degradation process [6-11]. In manufacturing industries, the corrosion of machinery and equipment can lead to disruptions in production schedules and increased maintenance expenditures.

The energy sector also grapples with corrosion-related challenges, particularly in oil and gas exploration, production, and transportation. Pipelines, platforms, and vessels are susceptible to corrosion in harsh environments, impacting both the operational efficiency and safety of these critical components. These statistics and examples underscore the pervasive nature of corrosion-related challenges across diverse sectors, emphasizing the urgent need for effective corrosion prevention strategies. The exploration of corrosion inhibitors, such as Schiff bases, becomes imperative in this context, as it holds the potential to mitigate the economic and environmental impacts associated with this widespread and persistent phenomenon [12-15]. Corrosion inhibitors play a pivotal role in the ongoing battle against the detrimental effects of corrosion. As a natural process,

corrosion poses a significant threat to the integrity and functionality of metal structures and components across various industries. Corrosion inhibitors are chemical compounds designed to mitigate or prevent the corrosion of metals by forming a protective layer on the metal surface. This layer acts as a barrier, impeding the corrosive agents' access and reducing the oxidation reactions that lead to corrosion. The significance of corrosion inhibitors lies in their ability to prolong the lifespan of metal structures and components [16-19]. By inhibiting corrosion, these compounds contribute to the preservation of infrastructure, machinery, and equipment, leading to extended service life and reduced maintenance costs. In addition to their protective role, corrosion inhibitors enhance the safety and reliability of critical systems, ensuring they can operate efficiently over an extended period. The economic implications of corrosion prevention are substantial. The costs associated with repairing or replacing corroded components, conducting maintenance, and addressing downtime due to corrosion-related failures are significant contributors to financial losses for industries. Corrosion inhibitors offer a cost-effective solution by providing a proactive means of protecting assets and reducing the frequency and severity of corrosion-related issues. In the long run, the investment in corrosion inhibitors translates into substantial savings, making them a crucial component of corrosion management strategies [20-24].

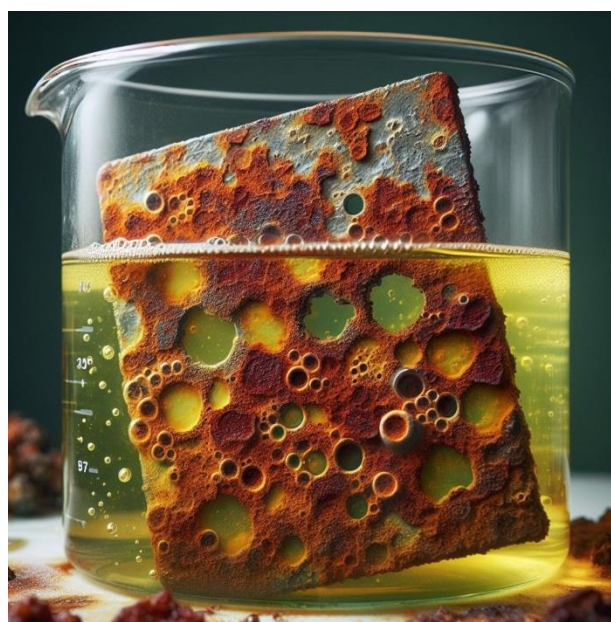

**Fig. 1.** Steel corrosion corrosives solution.

Schiff bases represent a versatile class of organic compounds characterized by their diverse chemical structures and reactivity. Derived from the condensation reaction between a primary amine and a carbonyl compound, Schiff bases exhibit a wide range of properties that make them intriguing candidates for various applications. In the context of corrosion inhibition, Schiff bases have garnered attention for their potential to form protective films on metal surfaces.


The historical context of Schiff bases traces back to the pioneering work of Hugo Schiff in the late 19th century. Initially explored for their coordination chemistry, Schiff bases have evolved to find applications not only in corrosion inhibition but also in medicinal chemistry, catalysis, and other areas. Their adaptability and ability to undergo structural modifications make them particularly appealing for addressing corrosion challenges in different industrial settings [25-34]. The selection of Schiff bases as the focal point for this mini-review stems from their unique and promising attributes that position them as compelling candidates in the realm of corrosion inhibition. Schiff bases exhibit a remarkable versatility in terms of their chemical structure, allowing for tailored modifications to enhance their efficacy as corrosion inhibitors. Their ability to form stable complexes with metal ions and surfaces presents a distinct advantage in impeding the corrosive processes that compromise the integrity of metals. The dynamic nature of Schiff bases, characterized by the presence of azomethine (-C=N-) groups, contributes to their reactivity and responsiveness to various environmental conditions. These distinctive features make Schiff bases an intriguing subject of study for their potential to provide effective and customizable solutions to the complex challenges posed by corrosion [1,11,35-38].

Table 1 compares Schiff bases with traditional corrosion inhibitors, highlighting their mechanisms of action, advantages, and disadvantages. While Schiff bases offer versatility and potential dual functionality, challenges such as stability and selectivity should be addressed. Inorganic inhibitors may excel in stability but lack structural diversity, while organic inhibitors provide broad applicability with potential toxicity concerns.

**Table 1:** Comparative analysis of schiff bases and traditional corrosion inhibitors.

Corrosion Inhibitor Type	Mechanism of Action	Pros	Cons
Schiff Bases	Adsorption on metal surface, formation of protective film	Versatile structural modifications, potential for dual functionality	Stability concerns, selectivity challenges
Inorganic Inhibitors	Formation of insoluble precipitates on metal surface	High stability, effective in specific environments	Limited structural diversity, environmental impact
Organic Inhibitors	Adsorption on metal surface, film formation	Widely applicable, stability in various environments	Limited structural diversity, potential toxicity

Moreover, Schiff bases have demonstrated the capacity to offer dual functionalities in corrosion inhibition. Beyond the formation of protective films on metal surfaces, they often possess inherent antioxidant properties, further bolstering their ability to counteract oxidative reactions that contribute to corrosion. This dual mechanism sets Schiff bases apart from conventional corrosion inhibitors, making them an innovative and holistic approach to corrosion prevention [23,28,39-42].

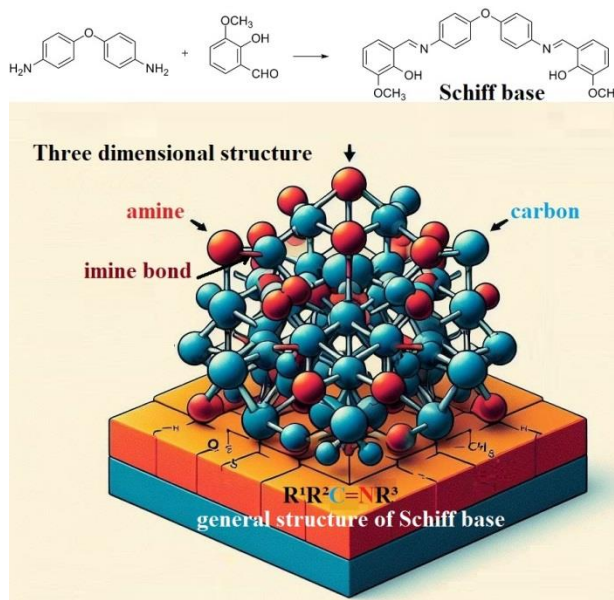

**Fig. 2.** General structure of Schiff bases.

In Figure 2, we present the fundamental structure of Schiff bases, showcasing the typical formation through the condensation reaction between a

primary amine and a carbonyl compound. This visual representation serves as a foundation for understanding the diverse chemical structures of Schiff bases, a key aspect that influences their corrosion inhibition properties.

The primary objective of this mini-review is to comprehensively explore the role of Schiff bases as corrosion inhibitors, shedding light on their mechanisms, recent advancements, and potential applications. The specific goals include:

- **Synthesis and Structure:** Investigate the synthesis methods and structural characteristics of Schiff bases that influence their corrosion inhibition properties.
- **Mechanism of Corrosion Inhibition:** Delve into the underlying mechanisms through which Schiff bases act as corrosion inhibitors, emphasizing their interactions with metal surfaces.
- **Recent Advances:** Highlight recent research findings and innovations in the field, showcasing novel Schiff base modifications that exhibit enhanced corrosion inhibition efficiency.
- **Applications:** Explore practical applications of Schiff bases as corrosion inhibitors, examining their compatibility with different metals and environmental conditions.
- **Challenges and Future Directions:** Discuss challenges and limitations associated with Schiff bases as corrosion inhibitors and provide insights into potential future research directions.

## 2. STRUCTURE AND SYNTHESIS OF SCHIFF BASES

### 2.1 General structure of Schiff bases

Schiff bases, a class of organic compounds, are characterized by a distinctive structure formed through the condensation reaction between a primary amine ( $-NH_2$ ) and a carbonyl compound (aldehyde or ketone). The key feature of Schiff bases is the azomethine ( $-C=N-$ ) linkage, resulting from the nucleophilic addition of the amine group to the carbonyl group. This structure imparts unique properties to Schiff bases, making them versatile compounds with significant applications, including corrosion

inhibition. The general structure of Schiff bases, as depicted in Figure 2, illustrates the double bond ( $-C=N-$ ) formed during the condensation reaction. This structure not only serves as the basis for their corrosion inhibition properties but also influences their reactivity and coordination abilities, contributing to their diverse applications in chemistry and biology [1,11,12,23,28].

### 2.2 Methods of synthesis of Schiff bases

The synthesis of Schiff bases is typically achieved through the condensation reaction between a primary amine and a carbonyl compound. Commonly employed methods include [1,11,12,23,28, 43,44]:

- **Classic Schiff Base Formation:** Involves mixing an aldehyde or ketone with a primary amine under mild conditions. This reaction can be catalyzed by acid or base, promoting the formation of the azomethine linkage.
- **Microwave-Assisted Synthesis:** Utilizes microwave irradiation to accelerate the condensation reaction, reducing reaction times and improving yields.
- **Green Synthesis:** Involves using environmentally friendly solvents and catalysts, aligning with sustainable chemistry principles.

The choice of synthesis method depends on factors such as reaction conditions, efficiency, and environmental considerations. Microwave-assisted and green synthesis methods have gained prominence for their efficiency and eco-friendly characteristics.

### 2.3 Versatility of Schiff bases in structural modification

Schiff bases exhibit remarkable versatility in terms of structural modification, allowing for tailoring their properties to suit specific applications. Structural modification can be achieved through [45-48]:

- **Substitution of Aromatic Rings:** Altering the aromatic rings in the Schiff base structure to influence its electronic and steric properties.
- **Functional Group Introductions:** Introducing various functional groups to enhance specific chemical interactions or improve solubility.



- **Metal Complexation:** Forming metal complexes by coordinating Schiff bases with metal ions, leading to enhanced properties such as increased stability and reactivity.

The ability to modify the structure of Schiff bases provides researchers with a toolbox for designing compounds with optimized corrosion inhibition properties. Structural tailoring allows for fine-tuning the electronic and steric features, impacting the interactions with metal surfaces and, consequently, the efficacy as corrosion inhibitors. This versatility positions Schiff bases as promising candidates for addressing the multifaceted challenges associated with corrosion in diverse environments.

### 3. MECHANISM OF CORROSION INHIBITION

Corrosion inhibition by Schiff bases involves a multifaceted mechanism that capitalizes on their unique chemical properties. Understanding this mechanism is crucial for appreciating the efficacy of Schiff bases in preventing metal degradation. Figure 3 elucidates the mechanism through which Schiff bases act as corrosion inhibitors. It illustrates the interaction between Schiff bases and metal surfaces, emphasizing the formation of a protective film that impedes corrosive processes. This visual depiction aids in conveying the intricacies of the corrosion inhibition process facilitated by Schiff bases.

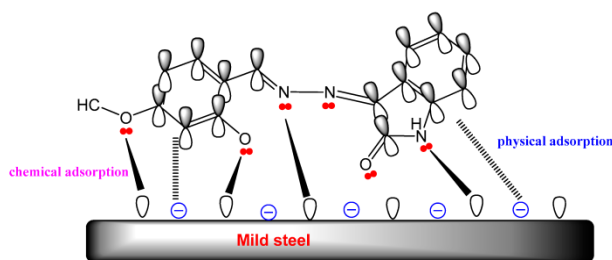


Fig. 2. Mechanism of corrosion inhibition by Schiff bases.

#### 3.1 Elaboration on the mechanism

Schiff bases act as corrosion inhibitors primarily by forming a protective layer on the metal surface. This layer inhibits the access of corrosive agents to the metal, thereby slowing down or preventing the oxidation reactions that lead to corrosion. The reactive centers, such as the azomethine ( $-C=N-$ ) group in Schiff bases, play a pivotal role in adsorbing onto the metal surface, forming a stable

and insoluble protective film. This adsorption process is dynamic and reversible, allowing Schiff bases to continuously interact with the metal surface, ensuring long-lasting corrosion protection [1,11,12,23,28].

#### 3.2 Interaction with metal surfaces

The interaction of Schiff bases with metal surfaces is characterized by adsorption phenomena. The functional groups present in Schiff bases, such as the nitrogen atoms from the azomethine group, readily coordinate with metal ions on the surface, leading to the formation of a coordinated protective layer. This interaction not only impedes the penetration of corrosive species but also stabilizes the metal surface, reducing the likelihood of further oxidation [49-51].

#### 3.3 Unique features in comparison to other corrosion inhibitors

Schiff bases exhibit several unique features that set them apart from conventional corrosion inhibitors. One notable aspect is their versatility in structural modification. The ability to tailor the chemical structure of Schiff bases allows for fine-tuning their corrosion inhibition properties, optimizing their effectiveness for specific metal types and environmental conditions. Additionally, the presence of multiple functional groups in Schiff bases often imparts them with antioxidant properties, providing a dual mechanism of protection against both chemical and electrochemical corrosion. Furthermore, the reversible nature of the adsorption process allows Schiff bases to form a dynamic equilibrium with the metal surface, responding to changes in the corrosion environment. This adaptability is a distinct advantage, especially in fluctuating conditions where other inhibitors might exhibit limited efficacy [52-59].

In summary, the corrosion inhibition mechanism of Schiff bases involves the formation of a protective layer through dynamic adsorption onto metal surfaces. Their unique chemical structure and interaction dynamics distinguish them as effective corrosion inhibitors, offering advantages over traditional methods. The reversible nature of their adsorption, coupled with the potential for structural modification, contributes to the versatility and efficacy of Schiff bases in corrosion prevention.

#### 4. RECENT ADVANCES IN SCHIFF BASES AS CORROSION INHIBITORS

Recent research in the field of corrosion inhibition has witnessed significant advancements pertaining to Schiff bases. These developments not only deepen our understanding of the corrosion inhibition mechanism but also pave the way for novel applications and improved efficiency [60-65].

##### 4.1 Summary of recent research findings

Recent studies have focused on elucidating the specific mechanisms underlying Schiff bases' corrosion inhibition properties. Advanced spectroscopic and computational techniques have been employed to unravel the intricacies of the adsorption process on metal surfaces. Additionally, there has been a concerted effort to explore the applicability of Schiff bases across diverse metal substrates and in various corrosive environments [66,67].

##### 4.2 Novel Schiff bases and modifications

Excitingly, several novel Schiff bases and modified derivatives have demonstrated

enhanced corrosion inhibiting properties. Researchers have designed Schiff bases with tailored chemical structures, optimizing functionalities that contribute to stronger adsorption onto metal surfaces. These modifications often involve introducing electron-donating or electron-withdrawing groups to fine-tune the electronic and steric properties of the Schiff base, influencing its adsorption affinity and overall corrosion inhibition efficiency. One noteworthy advancement involves the incorporation of nanomaterials into Schiff bases, creating hybrid compounds that exhibit synergistic effects. Nanocomposites of Schiff bases have shown superior corrosion inhibition compared to their individual components, opening new avenues for multifunctional and highly efficient corrosion inhibitors [68-72].

Table 2 summarizes recent studies on Schiff bases as corrosion inhibitors, emphasizing novel compounds and modifications. The hybrid nanocomposite demonstrates improved stability, while nitrogen-rich Schiff bases and self-healing functionality showcase enhanced corrosion inhibition efficiency and prolonged protection, respectively. Synthesis methods play a crucial role in tailoring properties for specific applications.

**Table 2.** Recent advances in Schiff bases as corrosion inhibitors.

Novel Schiff Base/Modification	Synthesis Method	Enhanced Properties	Key Findings
Hybrid Schiff base-nanocomposite	Sol-gel method	Improved stability, enhanced adsorption	Effective in harsh environments
Nitrogen-rich Schiff base with electron-donating group	Microwave-assisted synthesis	Increased corrosion inhibition efficiency	Structural modification influences performance
Schiff base with self-healing functionality	Electrochemical deposition	Self-healing film formation	Prolonged protection, potential for autonomous repair

##### 4.3 Corrosion inhibition efficiency

Studies exploring the relationship between the structural features of Schiff bases and their corrosion inhibition efficiency have garnered substantial attention. Researchers have systematically varied the substituents, backbone structure, and functional groups in Schiff bases to discern the impact on adsorption strength, film formation, and overall protective performance. Quantitative structure-activity relationship (QSAR) studies have emerged, aiming to establish predictive models that correlate specific structural attributes of Schiff bases with their corrosion

inhibition efficacy. These investigations provide valuable insights for the rational design of new Schiff base derivatives with tailored properties for enhanced corrosion protection. In conclusion, recent advances in Schiff bases as corrosion inhibitors encompass a thorough exploration of their mechanisms, the introduction of novel compounds with improved properties, and a deeper understanding of the structure-activity relationship. These findings propel Schiff bases to the forefront of corrosion inhibition research, holding promise for the development of highly effective and tailored inhibitors with broad industrial applications [73-77].

## 5. CHARACTERIZATION TECHNIQUES

Characterizing the interaction between Schiff bases and metal surfaces is essential for understanding their effectiveness as corrosion inhibitors. Various analytical techniques are employed to explore the adsorption process, film formation, and the overall impact of Schiff bases on the corrosion behavior of metals [78-92].

### 5.1 Spectroscopic techniques

Spectroscopic methods play a crucial role in characterizing the interaction between Schiff bases and metal surfaces.

- **Infrared Spectroscopy (FT-IR):** FT-IR is commonly used to identify functional groups and ascertain molecular vibrations. In the context of corrosion inhibition, it helps in detecting changes in the Schiff base's chemical structure upon adsorption onto metal surfaces.
- **UV-Visible Spectroscopy:** UV-Visible spectroscopy aids in monitoring changes in the electronic structure of Schiff bases during the corrosion inhibition process. Shifts in absorption peaks provide insights into the formation and stability of the protective film.

### 5.2 Electrochemical techniques

Electrochemical methods are instrumental in evaluating the electrochemical behavior of metal surfaces in the presence of Schiff bases [93-102].

- **Potentiodynamic Polarization:** This technique involves measuring the current-voltage relationship to assess the corrosion rate of metals. Schiff bases can alter the polarization curves, indicating their impact on the kinetics of corrosion reactions.
- **Electrochemical Impedance Spectroscopy (EIS):** EIS measures the response of a metal interface to a small alternating current. Changes in impedance parameters help in understanding the corrosion inhibition mechanism and the protective efficiency of Schiff bases.

### 5.3 Surface Analysis Techniques

Surface analysis techniques provide direct insights into the morphology and composition of the protective film formed by Schiff bases [103-113].

- **Scanning Electron Microscopy (SEM):** SEM enables the visualization of the metal surface morphology before and after exposure to the Schiff base. It helps in assessing the film's coverage, uniformity, and any alterations induced by the corrosion inhibition process.
- **X-ray Photoelectron Spectroscopy (XPS):** XPS is used to determine the elemental composition and chemical states of the metal surface and the adsorbed species. It provides detailed information on the composition of the protective layer formed by Schiff bases.
- **Atomic Force Microscopy (AFM):** AFM offers high-resolution imaging of the metal surface, allowing for the visualization of nanoscale features and changes induced by the adsorption of Schiff bases.

In summary, the combination of spectroscopic, electrochemical, and surface analysis techniques provides a comprehensive understanding of the interaction between Schiff bases and metal surfaces. These methods contribute to the elucidation of the corrosion inhibition mechanism and the assessment of the protective performance of Schiff bases in diverse corrosive environments.

## 6. APPLICATIONS OF SCHIFF BASES AS CORROSION INHIBITORS

Schiff bases have demonstrated immense potential as corrosion inhibitors, offering a versatile and effective solution across various industries. Their unique chemical properties and reactivity make them applicable to diverse metal substrates and corrosive environments [114-117]. Table 3 assesses the compatibility of Schiff bases with various metal substrates and environmental conditions. Schiff bases exhibit high inhibition efficiency on iron, but performance varies on aluminum and copper. The effectiveness is influenced by structural modifications and the specific corrosive environment, providing insights for tailored applications.

**Table 3.** Compatibility of Schiff bases with different metals and environments.

Metal Substrate	Corrosion Inhibition Efficiency of Schiff Bases	Environmental Conditions	Key Observations
Iron	High	Neutral pH, atmospheric exposure	Effective protective film formation
Aluminum	Moderate	Alkaline conditions, marine environment	Structural modifications influence performance
Copper	Low	Acidic conditions, high humidity	Challenges in achieving consistent inhibition

### 6.1. Manufacturing industry

In the manufacturing sector, Schiff bases find applications as corrosion inhibitors for metal components and machinery. The inhibitory action of Schiff bases helps mitigate the corrosive effects of industrial processes and environmental conditions, thereby extending the lifespan of equipment, reducing maintenance costs, and enhancing overall operational efficiency.

### 6.2. Infrastructure and construction

Schiff bases are utilized in the protection of critical infrastructure, including bridges, pipelines, and buildings. The compatibility of Schiff bases with different construction materials, such as steel and reinforced concrete, makes them valuable in preventing corrosion-induced structural deterioration. This application is particularly significant in environments with high humidity, salt exposure, or chemical pollutants.

### 6.3. Oil and gas industry

In the oil and gas sector, where corrosion poses a significant challenge, Schiff bases serve as effective inhibitors for pipelines, storage tanks, and offshore platforms. Their ability to withstand harsh conditions, including exposure to corrosive fluids and atmospheric elements, makes them a valuable asset in protecting vital components within the industry [118-120].

### 6.4. Automotive and transportation

Schiff bases contribute to the corrosion protection of automotive components and transportation infrastructure. They can be incorporated into coatings for vehicles, railway systems, and maritime vessels,

safeguarding against environmental factors, road salts, and corrosive agents encountered during transportation.

### 6.5. Aerospace applications

Schiff bases play a role in safeguarding metal components in the aerospace industry. Their compatibility with materials commonly used in aircraft construction makes them suitable for protecting critical parts against corrosion in aerospace environments characterized by extreme temperatures, humidity fluctuations, and exposure to atmospheric contaminants.

### 6.6. Compatibility with various metals and environments

One of the key advantages of Schiff bases is their compatibility with a wide range of metals, including iron, steel, aluminum, and copper. Their effectiveness extends to both ferrous and non-ferrous alloys, enhancing their versatility in diverse industrial applications.

Schiff bases exhibit favorable performance in various environmental conditions, from marine and coastal areas to industrial settings with aggressive chemical exposures. Their corrosion inhibition efficiency remains notable in acidic, alkaline, and neutral pH environments, showcasing their adaptability to different contexts.

In conclusion, the applications of Schiff bases as corrosion inhibitors are broad and diverse, spanning multiple industries. Their compatibility with various metals and environments positions them as valuable assets in the ongoing efforts to combat corrosion, contributing to the longevity and reliability of critical infrastructure and industrial components.



## 7. CHALLENGES AND FUTURE PERSPECTIVES:

The use of Schiff bases as corrosion inhibitors, while promising, is not without its challenges. Understanding and addressing these challenges are essential for advancing their practical applications and further optimizing their performance.

### 7.1. Challenges and limitations

- **Stability and Reactivity:** Schiff bases may undergo hydrolysis under certain conditions, limiting their stability. The reactivity of Schiff bases can also vary depending on the nature of the metal substrate and the corrosive environment, posing challenges in achieving consistent and reliable corrosion inhibition.
- **Selectivity:** Schiff bases may exhibit selectivity in their inhibitory action, being more effective for certain metals or environments than others. Achieving broad-spectrum corrosion protection across different alloys and exposure conditions remains a challenge.
- **Long-Term Performance:** The long-term performance and durability of Schiff bases as corrosion inhibitors require further investigation. Understanding the sustained effectiveness of Schiff bases over extended periods and under cyclic environmental conditions is crucial for real-world applications.

### 7.2. Future research directions

**Structural Optimization:** Future research efforts can focus on refining the chemical structure of Schiff bases to enhance their corrosion inhibition efficiency. This may involve exploring new synthetic routes, introducing specific functional groups, or incorporating nanomaterials to create hybrid compounds with improved properties.

**In-Depth Mechanistic Studies:** A deeper understanding of the mechanistic aspects of Schiff bases in corrosion inhibition is essential. Advanced spectroscopic and computational techniques can be employed to unravel the intricacies of their interaction with metal surfaces, providing insights that inform the design of more effective inhibitors.

**Environmental Compatibility:** Research can delve into tailoring Schiff bases for compatibility with a broader range of environmental conditions. This includes investigating their performance in extreme temperatures, high salinity, and other challenging settings to expand their applicability across diverse industries.

**Multifunctional Inhibitors:** Exploring the development of Schiff bases with additional functionalities, such as self-healing properties or dual corrosion and fouling inhibition, can lead to the creation of multifunctional inhibitors that address multiple challenges simultaneously.

**Field Testing and Validation:** Conducting extensive field testing and validation studies in real-world industrial settings is crucial to verifying the performance of Schiff bases under practical conditions. This step is essential for bridging the gap between laboratory research and practical applications.

### 7.3. Collaboration and interdisciplinary approaches

Promoting collaboration between corrosion scientists, materials scientists, chemists, and engineers is vital for advancing research on Schiff bases as corrosion inhibitors. Interdisciplinary approaches can facilitate a comprehensive understanding of their behavior and performance, leading to innovative solutions and breakthroughs in corrosion prevention.

In conclusion, while Schiff bases show immense promise as corrosion inhibitors, overcoming challenges and exploring new research directions are imperative for their widespread and effective application in various industries. By addressing these challenges and embracing interdisciplinary collaborations, researchers can pave the way for the development of advanced Schiff base-based corrosion inhibitors with enhanced stability, selectivity, and long-term performance.

## 6. CONCLUSION

In conclusion, the exploration of Schiff bases as corrosion inhibitors presents a compelling avenue for mitigating the pervasive and economically burdensome effects of corrosion across diverse industries. This mini-review has provided a comprehensive overview, beginning with the urgent need for corrosion inhibitors in the face of escalating economic and environmental consequences. The general structure of Schiff bases, characterized by their dynamic chemical composition and the azomethine group, positions them as versatile candidates for corrosion inhibition. The synthesis methods employed in their preparation, ranging from traditional routes to innovative nanocomposite approaches, highlight the adaptability and potential for structural modification. Delving into the mechanism of corrosion inhibition, we uncovered the dynamic interaction between Schiff bases and metal surfaces, leading to the formation of protective layers. Unique features, such as the reversible adsorption process and dual functionalities, distinguish Schiff bases from conventional inhibitors.

Recent advances in the field underscore the dynamism of research, with novel Schiff bases and modifications showcasing enhanced corrosion inhibition properties. Studies exploring the relationship between their structure and efficiency open avenues for tailored design and optimization. However, challenges remain, including issues of stability, selectivity, and the need for long-term performance studies. Future research directions should focus on structural optimization, in-depth mechanistic studies, and environmental compatibility to address these challenges and elevate the practical applicability of Schiff bases. In navigating the path forward, collaboration and interdisciplinary approaches are key. Field testing, validation studies, and the integration of findings from corrosion science, materials science, and chemistry will bridge the gap between theoretical promise and practical implementation. In essence, Schiff bases emerge as promising corrosion inhibitors, and their potential impact extends across manufacturing, infrastructure, energy, and beyond. As research advances, the journey toward innovative, effective, and sustainable corrosion prevention continues, fueled by the dynamic and versatile nature of Schiff bases.

## REFERENCES

- [1] B. S. Mahdi *et al.*, "Corrosion inhibition of mild steel in hydrochloric acid environment using terephthaldehyde based on Schiff base: gravimetric, thermodynamic, and computational studies," *Molecules*, vol. 27, no. 15, p. 4857, Jul. 2022, doi: 10.3390/molecules27154857
- [2] Q. Jawad, D. Zinad, R.D. Salim, A.A. Al-Amiery, T.S. Gaaz, M.S. Takriff and A. Kadhum, "Synthesis, Characterization, and Corrosion Inhibition Potential of Novel Thiosemicarbazone on Mild Steel in Sulfuric Acid Environment," *Coatings*, 2019, 9, 729. doi: 10.3390/coatings9110729
- [3] S. Al-Baghdadi, F. Noori, W.K. Ahmed and A.A. Al-Amiery, "Thiadiazole as a potential corrosion inhibitor for mild steel in 1 M HCl," *J. Adv. Electrochem.*, 2016, 2, 67–69.
- [4] A.M. Resen, M. Hanoon, R.D. Salim, A.A. Al-Amiery, L.M. Shaker and A.A.H. Kadhum, "Gravimetric, theoretical, and surface morphological investigations of corrosion inhibition effect of 4-(benzimidazole-2-yl) pyridine on mild steel in hydrochloric acid," *Koroze Ochr. Mater.*, 2020, 64, 122–130. doi: 10.2478/kom-2020-0018
- [5] S. Junaedi, A. Al-Amiery, A. Kadhum, A. Kadhum and A. Mohamad, "Inhibition effects of a synthesized novel 4-aminoantipyrine derivative on the corrosion of mild steel in hydrochloric acid solution together with quantum chemical studies," *Int. J. Mol. Sci.*, 2013, 14, 11915–11928. doi: 10.3390/ijms140611915
- [6] M.M. Solomon, I.E. Uzoma, J.A.O. Olugbuyiro and O.T. Ademosun, "A Censorious Appraisal of the Oil Well Acidizing Corrosion Inhibitors," *J. Pet. Sci. Eng.*, 2022, 215, 110711. doi: 10.1016/j.petrol.2022.110711
- [7] D. Wang, Y. Li, B. Chen and L. Zhang, "Novel Surfactants as Green Corrosion Inhibitors for Mild Steel in 15% HCl: Experimental and Theoretical Studies," *Chem. Eng. J.*, 2020, 402, 126219. doi: 10.1016/j.cej.2020.126219
- [8] B. El-Haitout, I. Selatnia, H. Lgaz, M.R. Al-Hadeethi, H.-S. Lee, A. Chaouiki, Y.G. Ko, I.H. Ali and R. Salghi, "Exploring the Feasibility of New Eco-Friendly Heterocyclic Compounds for Establishing Efficient Corrosion Protection for N80 Steel in a Simulated Oil Well Acidizing Environment: From Molecular-Level Prediction to Experimental Validation," *Colloids Surf. A*, 2023, 656, 130372. doi: 10.1016/j.colsurfa.2022.130372

- [9] B.D.B. Tiu and R.C. Advincula, "Polymeric Corrosion Inhibitors for the Oil and Gas Industry: Design Principles and Mechanism," *React. Funct. Polym.*, 2015, 95, 25–45. doi: 10.1016/j.reactfunctpolym.2015.08.006.
- [10] A.H. Alamri, "Localized Corrosion and Mitigation Approach of Steel Materials Used in Oil and Gas Pipelines – An Overview," *Eng. Failure Anal.*, 2020, 116, 104735. doi: 10.1016/j.engfailanal.2020.104735
- [11] D.S. Chauhan, M.A.J. Mazumder, M.A. Quraishi and K.R. Ansari, "Chitosan-Cinnamaldehyde Schiff Base: A Bioinspired Macromolecule as Corrosion Inhibitor for Oil and Gas Industry," *Int. J. Biol. Macromol.*, 2020, 158, 127–138. doi: 10.1016/j.ijbiomac.2020.04.200
- [12] S. Şafak, B. Duran, A. Yurt and G. Türkoğlu, "Schiff Bases as Corrosion Inhibitor for Aluminium in HCl Solution," *Corros. Sci.*, 2012, 54, 251–259. doi: 10.1016/j.corsci.2011.09.026
- [13] F.E.-T. Heikal and A.E. Elkholy, "Gemini Surfactants as Corrosion Inhibitors for Carbon Steel," *J. Mol. Liq.*, 2017, 230, 395–407. doi: 10.1016/j.molliq.2017.01.047
- [14] M. Farsak, H. Keleş and M.A. Keleş, "New Corrosion Inhibitor for Protection of Low Carbon Steel in HCl Solution," *Corros. Sci.*, 2015, 98, 223–232. doi: 10.1016/j.corsci.2015.05.036
- [15] Alamiery, W.N.R.W. Isahak, H.S.S. Aljibori, H.A. Al-Asadi and A.A.H. Kadhum, "Effect of the structure, immersion time and temperature on the corrosion inhibition of 4-pyrrol-1-yl-n-(2,5-dimethyl-pyrrol-1-yl)benzoylamine in 1.0 M HCl solution," *Int. J. Corros. Scale Inhib.*, 2021, 10, no. 2, 700–713. doi: 10.17675/2305-6894-2021-10-2-14
- [16] S. Al-Baghdadi, F. Hashim, A. Salam, T. Abed, T. Gaaz, A. Al-Amiery, A.H. Kadhum, K. Reda and W. Ahmed, "Synthesis and corrosion inhibition application of NATN on mild steel surface in acidic media complemented with DFT studies," *Results Phys.*, 2018, 8, 1178–1184. doi: 10.1016/j.rinp.2018.02.007
- [17] W.K. Al-Azzawi, A.J. Al Adily, F.F. Sayyid, R.K. Al-Azzawi, M.H. Kzar, H.N. Jawoosh, A.A. Al-Amiery, A.A.H. Kadhum, W.N.R.W. Isahak and M.S. Takriff, "Evaluation of corrosion inhibition characteristics of an N-propionanilide derivative for mild steel in 1 M HCl: Gravimetric and computational studies," *Int. J. Corros. Scale Inhib.*, 2022, 11, no. 3, 1100–1114. doi: 10.17675/2305-6894-2022-11-3-12
- [18] A. Mustafa, F. Sayyid, N. Betti, M. Hanoon, A. Al-Amiery, A. Kadhum and M. Takriff, "Inhibition Evaluation of 5-(4-(1H-pyrrol-1-yl)phenyl)-2-mercapto-1,3,4-oxadiazole for the Corrosion of Mild Steel in an Acid environment: Thermodynamic and DFT Aspects," *Tribologia*, 2021, 38, 39–47. doi: 10.30678/ft.105330
- [19] Y.M. Abdulsahib, A.J.M. Eltmimi, S.A. Alhabeeb, M.M. Hanoon, A.A. Al-Amiery, T. Allami and A.A.H. Kadhum, "Experimental and theoretical investigations on the inhibition efficiency of N-(2,4-dihydroxytolueneylidene)-4-methylpyridin-2-amine for the corrosion of mild steel in hydrochloric acid," *Int. J. Corros. Scale Inhib.*, 2021, 10, no. 3, 885–899. doi: 10.17675/2305-6894-2021-10-3-3
- [20] A.K. Khudhair, A.M. Mustafa, M.M. Hanoon, A. Al-Amiery, L.M. Shaker, T. Gazz, A.B. Mohamad, A.H. Kadhum and M.S. Takriff, "Experimental and Theoretical Investigation on the Corrosion Inhibitor Potential of N-MEH for Mild Steel in HCl," *Prog. Color, Color. Coat.*, 2022, 15, 111–122. doi: 10.30509/PCCC.2021.166815.1111
- [21] D.S. Zinad, R.D. Salim, N. Betti, L.M. Shaker and A.A. AL-Amiery, "Comparative Investigations of the Corrosion Inhibition Efficiency of a 1-phenyl-2-(1-phenylethylidene)hydrazine and its Analog Against Mild Steel Corrosion in Hydrochloric Acid Solution," *Prog. Color, Color. Coat.*, 2022, 15, 53–63. doi: 10.30509/pccc.2021.166786.1108
- [22] R.D. Salim, N. Betti, M. Hanoon and A.A. Al-Amiery, "2-(2,4-Dimethoxybenzylidene)-N-Phenylhydrazinocarbothioamide as an Efficient Corrosion Inhibitor for Mild Steel in Acidic Environment," *Prog. Color, Color. Coat.*, 2021, 15, 45–52. doi: 10.30509/pccc.2021.166775.1105
- [23] A. Naseef Jasim et al., "Schiff's Base Performance in Preventing Corrosion on Mild Steel in Acidic Conditions", *Prog. Color Colorants Coat.*, vol. 16, pp. 319-329, 2023. [Online]. Available: doi: 10.30509/pccc.2023.167081.1197
- [24] A.A. Al-Amiery, L.M. Shaker, A.H. Kadhum and M.S. Takriff, "Exploration of furan derivative for application as a corrosion inhibitor for mild steel in hydrochloric acid solution: Effect of immersion time and temperature on efficiency," *Mater. Today: Proc.*, 2021, 42, 2968–2973. doi: 10.1016/j.matpr.2020.12.807
- [25] A.M. Resen, M.M. Hanoon, W.K. Alani, A. Kadhim, A.A. Mohammed, T.S. Gaaz, A.A.H. Kadhum, A.A. Al-Amiery and M.S. Takriff, "Exploration of 8-piperazine-1-ylmethylumbelliferone for application as a corrosion inhibitor for mild steel in hydrochloric acid solution," *Int. J. Corros. Scale Inhib.*, 2021, 10, no. 1, 368–387. doi: 10.17675/2305-6894-2021-10-1-21

- [26] M.M. Hanoon, A.M. Resen, A.A. Al-Amiery, A.A.H. Kadhum and M.S. Takriff, "Theoretical and Experimental Studies on the Corrosion Inhibition Potentials of 2-((6-Methyl-2-Ketoquinolin-3-yl)Methylene) Hydrazinecarbothioamide for Mild Steel in 1 M HCl," *Prog. Color, Color. Coat.*, 2021, 15, 21–33. doi: 10.30509/PCCC.2020.166739.1095
- [27] F.G. Hashim, T.A. Salman, S.B. Al-Baghdadi, T. Gaaz and A.A. Al-Amiery, "Inhibition effect of hydrazine-derived coumarin on a mild steel surface in hydrochloric acid," *Tribologia*, 2020, 37, 45–53. doi: 10.30678/ft.95510
- [28] A. Alamiery, L.M. Shaker, T. Allami, A.H. Kadhum and M.S. Takriff, "A study of acidic corrosion behavior of Furan-Derived Schiff base for mild steel in hydrochloric acid environment: Experimental, and surface investigation," *Mater. Today: Proc.*, 2021, 44, 2337–2341. doi: 10.1016/j.matpr.2020.12.431
- [29] S. Al-Baghdadi, A. Al-Amiery, T. Gaaz and A. Kadhum, "Terephthalohydrazide and isophthalohydrazide as new corrosion inhibitors for mild steel in hydrochloric acid: Experimental and theoretical approaches," *Koroze Ochr. Mater.*, 2021, 65, 12–22. doi: 10.2478/kom-2021-0002
- [30] M.M. Hanoon, A.M. Resen, L.M. Shaker, A. Kadhum and A. Al-Amiery, "Corrosion investigation of mild steel in aqueous hydrochloric acid environment using n-(Naphthalen-1yl)-1-(4-pyridinyl)methanimine complemented with antibacterial studies," *Biointerface Res. Appl. Chem.*, 2021, 11, 9735–9743. doi: 10.33263/BRIAC112.97359743
- [31] S. Al-Baghdadi, T.S. Gaaz, A. Al-Adili, A. Al-Amiery and M. Takriff, "Experimental studies on corrosion inhibition performance of acetylthiophene thiosemicarbazone for mild steel in HCl complemented with DFT investigation," *Int. J. Low-Carbon Technol.*, 2021, 16, 181–188. doi: 10.1093/ijlct/ctaa050
- [32] A. Al-Amiery, "Anti-corrosion performance of 2-isonicotinoyl-nphenylhydrazinecarbothioamide for mild steel hydrochloric acid solution: Insights from experimental measurements and quantum chemical calculations," *Surf. Rev. Lett.*, 2021, 28, 2050058. doi: 10.1142/S0218625X20500584
- [33] A.A. Alamiery, "Investigations on the corrosion inhibitory effect of newly quinoline derivative on mild steel in HCl solution complemented with antibacterial studies," *Biointerface Res. Appl. Chem.*, 2022, 12, 1561–1568. doi: 10.33263/BRIAC122.15611568
- [34] A. Alamiery, "Short report of mild steel corrosion in 0.5 M H<sub>2</sub>SO<sub>4</sub> by 4-ethyl-1-(4-oxo-4-phenylbutanoyl)thiosemicarbazide," *Tribologi*, 2021, 30, 90–99.
- [35] A.A. Alamiery, W.N.R.W. Isahak and M.S. Takriff, "Inhibition of mild steel corrosion by 4-benzyl-1-(4-oxo-4-phenylbutanoyl)thiosemicarbazide: Gravimetric, adsorption and theoretical studies," *Lubricants*, 2021, 9, 93. doi: 10.3390/lubricants9090093
- [36] M.A. Dawood, Z.M.K. Alasady, M.S. Abdulazeez, D.S. Ahmed, G.M. Sulaiman, A.A.H. Kadhum, L.M. Shaker and A.A. Alamiery, "The corrosion inhibition effect of a pyridine derivative for low carbon steel in 1 M HCl medium: Complementated with antibacterial studies," *Int. J. Corros. Scale Inhib.*, 2021, 10, 1766–1782. doi: 10.17675/2305-6894-2021-10-4-25
- [37] A. Alamiery, "Corrosion inhibition effect of 2-N-phenylamino-5-(3-phenyl-3-oxo-1-propyl)-1,3,4-oxadiazole on mild steel in 1 M hydrochloric acid medium: Insight from gravimetric and DFT investigations," *Mater. Sci. Energy Technol.*, 2021, 4, 398–406. doi: 10.1016/j.mset.2021.09.002
- [38] A. Alamiery, "Anticorrosion effect of thiosemicarbazide derivative on mild steel in 1 M hydrochloric acid and 0.5 M sulfuric Acid: Gravimetric and theoretical studies," *Mater. Sci. Energy Technol.*, 2021, 4, 263–273. doi: 10.1016/j.mset.2021.07.004
- [39] A. Alamiery, W.N.R.W. Isahak, H. Aljibori, H. Al-Asadi and A. Kadhum, "Effect of the structure, immersion time and temperature on the corrosion inhibition of 4-pyrrol-1-yl-n-(2,5-dimethyl-pyrrol-1-yl)benzoylamine in 1.0 M HCl solution," *Int. J. Corros. Scale Inhib.*, 2021, 10, 700–713. doi: 10.17675/2305-6894-2021-10-2-14
- [40] C. Bannwarth, E. Caldeweyher, S. Ehlert, A. Hansen, P. Pracht, J. Seibert, S. Spicher and S. Grimme, "Extended tight-binding Quantum Chemistry Methods," *WIREs Comput. Mol. Sci.*, 2021, 11, 2. doi: 10.1002/wcms.1493
- [41] H. Chermette, "Chemical Reactivity Indexes in Density Functional Theory," *J. Comput. Chem.*, 1999, 20, no. 1, 129–154. doi: 10.1002/(SICI)1096-987X(19990115)20:13.0.CO;2-A
- [42] R. G. Parr and P. K. Chattaraj, "Principle of Maximum Hardness," *J. Am. Chem. Soc.*, vol. 113, no. 5, pp. 1854–1855, 1991. [Online]. Available: doi: 10.1021/ja00005a072
- [43] R. P. Iczkowski and J. L. Margrave, "Electronegativity," *J. Am. Chem. Soc.*, vol. 83, no. 17, pp. 3547–3551, 1961. [Online]. Available: doi: 10.1021/ja01478a001

- [44] W. K. Al-Azzawi et al., "Adsorption and theoretical investigations of a Schiff base for corrosion inhibition of mild steel in an acidic environment," *Int. J. Corros. Scale Inhib.*, vol. 11, no. 3, pp. 1063–1082, 2022. [Online]. Available: doi: 10.17675/2305-6894-2022-11-3-10
- [45] H. S. Aljibori et al., "The use of a Schiff base derivative to inhibit mild steel corrosion in 1 M HCl solution: a comparison of practical and theoretical findings," *Int. J. Corros. Scale Inhib.*, vol. 11, no. 4, pp. 1435–1455, 2022. [Online]. Available: doi: 10.17675/2305-6894-2022-11-4-2
- [46] A. Alamiery et al., "Corrosion inhibition of low-carbon steel in hydrochloric acid environment using a Schiff base derived from pyrrole: gravimetric and computational studies," *Int. J. Corros. Scale Inhib.*, vol. 10, pp. 749–765, 2021. [Online]. Available: doi: 10.17675/2305-6894-2021-10-2-17
- [47] A. J. M. Eltmimi et al., "Inhibitive effects of a novel efficient Schiff base on mild steel in hydrochloric acid environment," *Int. J. Corros. Scale Inhib.*, vol. 10, pp. 634–648, 2021. [Online]. Available: doi: 10.17675/2305-6894-2021-10-2-10
- [48] T. K. Chaitra et al., "Thermodynamic, Electrochemical and Quantum Chemical Evaluation of Some Triazole Schiff Bases as Mild Steel Corrosion Inhibitors in Acid Media," *J. Mol. Liq.*, vol. 211, pp. 1026–1038, 2015. [Online]. Available: doi: 10.1016/j.molliq.2015.08.031
- [49] R. G. Parr, L. V. Szentpály, and S. Liu, "Electrophilicity Index," *J. Am. Chem. Soc.*, vol. 121, no. 9, pp. 1922–1924, 1999. [Online]. Available: doi: 10.1021/ja983494x
- [50] N. P. Andreeva, Yu. I. Kuznetsov, and Kh. S. Shikhaliev, "The use of ellipsometry for studying adsorption of organic corrosion inhibitors from aqueous solutions on metals. Review. Part 1. Methods for obtaining adsorption isotherms," *Int. J. Corros. Scale Inhib.*, vol. 11, no. 4, pp. 1716–1723, 2022. [Online]. Available: doi: 10.17675/2305-6894-2022-11-4-20
- [51] Yu. I. Kuznetsov, "Organic corrosion inhibitors: where are we now? A review. Part I. Adsorption," *Int. J. Corros. Scale Inhib.*, vol. 4, no. 4, pp. 284–310, 2015. [Online]. Available: doi: 10.17675/2305-6894-2015-4-4-1
- [52] Ya. G. Bober, Yu. I. Kuznetsov, and N. P. Andreeva, "Adsorption at Iron and Passivation Effect of Anions of Substituted Phenylanthranilic Acids," *Prot. Met.*, vol. 44, no. 1, pp. 84–90, 2008. [Online]. Available: doi: 10.1134/S0033173208010116
- [53] Yu. I. Kuznetsov et al., "Joint adsorption of oleic and phenylanthranilic acids at passive iron," *Prot. Met.*, vol. 39, no. 5, pp. 462–467, 2003. [Online]. Available: doi: 10.1023/A:1025898803486
- [54] Yu. I. Kuznetsov et al., "On co-adsorption on passive iron from aqueous 1,2,3-benzotriazole and sodium phenylundecanoate," *Russ. J. Electrochem.*, vol. 46, no. 5, pp. 560–564, 2010. [Online]. Available: doi: 10.1134/S1023193510050101
- [55] K. Fukui, "Role of Frontier Orbitals in Chemical Reactions," *Science*, vol. 218, no. 4574, pp. 747–754, 1982. [Online]. Available: doi: 10.1126/science.218.4574.747
- [56] M. S. Abdulazeez et al., "Corrosion inhibition of low carbon steel in HCl medium using a thiadiazole derivative: weight loss, DFT studies and antibacterial studies," *Int. J. Corros. Scale Inhib.*, vol. 10, pp. 1812–1828, 2021. [Online]. Available: doi: 10.17675/2305-6894-2021-10-4-27
- [57] A. Z. Salman et al., "Selected BISThiadiazole: Synthesis and Corrosion Inhibition Studies on Mild Steel in HCL Environment," *Surf. Rev. Lett.*, vol. 27, p. 2050014, 2020. [Online]. Available: doi: 10.1142/S0218625X20500146
- [58] S. Varvara et al., "Evaluation of Some NonToxic Thiadiazole Derivatives as Bronze Corrosion Inhibitors in Aqueous Solution," *Corros. Sci.*, vol. 50, no. 9, pp. 2596–2604, 2008. [Online]. Available: doi: 10.1016/j.corosci.2008.06.046
- [59] H. Ibraheem et al., "4-Thiadiazole: The Biological Activities," *Sys. Rev. Pharm.*, vol. 9, no. 1, pp. 36–40, 2018. [Online]. Available: doi: 10.5530/srp.2018.1.7
- [60] A. Al-Amiery et al., "Green Antioxidants: Synthesis and Scavenging Activity of Coumarin Thiadiazoles as Potential Antioxidants Complemented by Molecular Modeling Studies," *Free Radicals Antioxid.*, vol. 6, no. 2, pp. 173–177, 2016. [Online]. Available: doi: 10.5530/fra.2016.2.7
- [61] R. G. Parr and R. G. Pearson, "Absolute Hardness: Companion Parameter to Absolute Electronegativity," *J. Am. Chem. Soc.*, vol. 105, no. 26, pp. 7512–7516, 1983. [Online]. Available: doi: 10.1021/ja00364a005
- [62] L. A. Khamaza, "Generalized Diagram of the Ultimate Nominal Stresses (Endurance Limit) and the Corresponding Dimensions of the Non-Propagating Fatigue Cracks for Sharp and Blunt Notches," *Strength Mater.*, vol. 51, no. 3, pp. 350–360, 2019. [Online]. Available: doi: 10.1007/s11223-019-00081-w
- [63] Yu. G. Matvienko, "Approaches of Fracture Mechanics in the Analysis of Admissible Defects



- in the Form of Notches," *Strength Mater.*, vol. 42, no. 1, pp. 58–63, 2010. [Online]. Available: doi: 10.1007/s11223-010-9188-2
- [64] D. Dwivedi et al., "Carbon steel corrosion: a review of key surface properties and characterization methods," *RSC Adv.*, vol. 7, pp. 4580–4610, 2017. [Online]. Available: doi: 10.1039/C6RA25094G
- [65] D. A. Winkler, "Predicting the performance of organic corrosion inhibitors," *Metals*, vol. 7, no. 12, p. 553, 2017. [Online]. Available: doi: 10.3390/met7120553
- [66] C. Verma, L. O. Olasunkanmi, E. E. Ebenso, and M. A. Quraishi, "Substituents effect on corrosion inhibition performance of organic compounds in aggressive ionic solutions: a review," *J. Mol. Liq.*, vol. 251, pp. 100–118, 2018. [Online]. Available: doi: 10.1016/j.molliq.2017.12.055
- [67] O. Kaczerewska et al., "Heteroatoms and  $\pi$  electrons as favorable factors for efficient corrosion protection," *Mater. Corros.*, vol. 70, pp. 1099–1110, 2019. [Online]. Available: doi: 10.1002/maco.201810570
- [68] Khezri, Adibe, Ladan Edjlali, Moosa Es' haggi, Mohammad Taghi Vardini, and Hadi Basharnavaz. "Addition of Schiff Bases to Hybrid Silane Sol–Gel Coatings: An Efficient Strategy to Develop an Active System for Corrosion Protection of Copper." *Journal of Materials Engineering and Performance* (2023): 1-10.
- [69] Mathew, Zachariah Pulluparampil, G. K. Shamnamol, K. P. Greeshma, and Sam John. "Insight on the corrosion inhibition of nanocomposite chitosan/boron nitride integrated epoxy coating system against mild steel." *Corrosion Communications* 9 (2023): 36-43.
- [70] Dardeer, Hemat M., Safaa A. Abbas, Mohamed Mohamady Ghobashy, Ghalia A. Gaber, and Moustafa F. Aly. "Synthesis and characterization of novel chitosan-sodium pyruvate polymer and its derivatives for corrosion feature evaluation of Cu-Ni alloy." *Inorganic Chemistry Communications* 157 (2023): 111308.
- [71] Alghamdi, Maha D. "Green nanomaterials and nanocomposites for corrosion inhibition applications." *Corrosion Reviews* 41, no. 3 (2023): 349-366.
- [72] Bijapur, Kiran, Vandana Molahalli, Apoorva Shetty, Arafat Toghan, Paola De Padova, and Gurumurthy Hegde. "Recent Trends and Progress in Corrosion Inhibitors and Electrochemical Evaluation." *Applied Sciences* 13, no. 18 (2023): 10107.
- [73] D. K. Verma, Y. Dewangan, A. K. Dewangan, and A. Asatker, "Heteroatom-Based Compounds as Sustainable Corrosion Inhibitors: An Overview," *J. Bio Tribo Corrosion*, vol. 7, pp. 1–18, 2021. [Online]. Available: doi: 10.1007/s40735-020-00447-7
- [74] M. Athar, H. Ali, and M. A. Quraishi, "Corrosion inhibition of carbon steel in hydrochloric acid by organic compounds containing heteroatoms," *Br. Corros. J.*, vol. 37, pp. 155–158, 2002. [Online]. Available: doi: 10.1179/000705902225002376
- [75] S. Hadisaputra et al., "(E)-ethyl 3-(4-methoxyphenyl) acrylate as corrosion inhibitor of iron in 1 M HCl solutions," *Int. J. Corros. Scale Inhib.*, vol. 7, no. 4, pp. 633–647, 2018. [Online]. Available: doi: 10.17675/2305-6894-2018-7-4-10
- [76] S. Hadisaputra et al., "(2R)-5-hydroxy-7-methoxy-2-phenyl-2,3-dihydrochromen-4-one as corrosion inhibitor for Iron in Hydrochloric Acid," *Int. J. Electrochem. Sci.*, vol. 14, pp. 11110–11121, 2019. [Online]. Available: doi: 10.20964/2019.12.77
- [77] S. Hadisaputra et al., "Pinostrobin as Copper Corrosion Inhibitor at 1 M H2SO4 Medium," *IOP Conf. Ser. Mater. Sci. Eng.*, vol. 833, p. 012010, 2020. [Online]. Available: doi: 10.1088/1757-899X/833/1/012010
- [78] C. Verma, L. O. Olasunkanmi, E. E. Ebenso, and M. A. Quraishi, "Substituents effect on corrosion inhibition performance of organic compounds in aggressive ionic solutions: a review," *J. Mol. Liq.*, vol. 251, pp. 100–118, 2018. [Online]. Available: doi: 10.1016/j.molliq.2017.12.055
- [79] S. Hadisaputra et al., "Theoretical study of the substituent effect on corrosion inhibition performance of benzimidazole and its derivatives," *Int. J. Corros. Scale Inhib.*, vol. 8, no. 3, pp. 673–688, 2019. [Online]. Available: doi: 10.17675/2305-6894-2019-8-3-15
- [80] K. Cao, W. Li, and L. Yu, "Investigation of 1-Phenyl-3-Methyl-5-Pyrazolone as a corrosion inhibitor for mild steel in 1 M hydrochloric acid," *Int. J. Electrochem. Sci.*, vol. 7, pp. 806–818, 2012.
- [81] Y. Zhang et al., "Corrosion Inhibition of Carbon Steel by 1-Phenyl-3-Amino-5-Pyrazolone in H2SO4 solution," *Int. J. Electrochem. Sci.*, vol. 14, pp. 999–1008, 2019. [Online]. Available: doi: 10.20964/2019.01.69
- [82] A. S. Fouda, A. A. Al-Sarawy, and E. E. El-Katori, "Pyrazolone derivatives as corrosion inhibitors for C-steel in hydrochloric acid solution," *Desalination*, vol. 201, pp. 1–13, 2006. [Online]. Available: doi: 10.1016/j.desal.2006.03.519

- [83] S. Hadisaputra et al., "ab initio MP2 and DFT studies of ethyl-p-methoxycinnamate and its derivatives as corrosion inhibitors of iron in acidic medium," *J. Phys.: Conf. Ser.*, vol. 1402, p. 055046, 2019. [Online]. Available: doi: 10.1088/1742-6596/1402/5/055046
- [84] V. S. Sastri and J. R. Perumareddi, "Molecular orbital theoretical studies of some organic corrosion inhibitors," *Corros. Sci.*, vol. 53, no. 8, pp. 617–622, 1997. [Online]. Available: doi: 10.5006/1.3290294
- [85] G. F. de Sousa et al., "Synthesis, spectroscopic studies and X-ray Crystal structures of new pyrazoline and pyrazole derivatives," *J. Chem. Crystallogr.*, vol. 41, pp. 401–408, 2011. [Online]. Available: doi: 10.1007/s10870-010-9896-2
- [86] S. Hadisaputra, Z. Iskandar, and D. Asnawati, "Prediction of the Corrosion Inhibition Efficiency of Imidazole Derivatives: A Quantum Chemical Study," *Acta Chim. Asiana*, vol. 2, no. 1, pp. 88–94, 2019. [Online]. Available: doi: 10.29303/aca.v2i1.15
- [87] N. O. Eddy, S. R. Stoyanov, and E. E. Ebenso, "Fluoroquinolones as corrosion inhibitors for mild steel in acidic medium; experimental and theoretical studies," *Int. J. Electrochem. Sci.*, vol. 5, pp. 1127–1150, 2010.
- [88] Y. Wirayani, M. Ulfa, and Y. Yahmin, "Corrosion inhibition efficiency of nicotine based on quantum chemical study," *Acta Chim. Asiana*, vol. 1, no. 2, pp. 37–42, 2018. [Online]. Available: doi: 10.29303/aca.v1i2.29
- [89] A. S. Fouda, M. A. Ismail, A. S. Abousalem, and G. Y. Elewady, "Experimental and theoretical studies on corrosion inhibition of 4-amidinophenyl-2,2'-bifuran and its analogues in acidic media," *RSC Adv.*, vol. 7, pp. 46414–46430, 2017. [Online]. Available: doi: 10.1039/C7RA08092A
- [90] ASTM International, "Standard Practice for Preparing, Cleaning, and Evaluating Corrosion Test," 2011, pp. 1–9.
- [91] G. R. Monama et al., "Hierarchical 4-tetranitro copper (II) phthalocyanine based metal organic framework hybrid composite with improved electrocatalytic efficiency towards hydrogen evolution reaction," *Results Phys.*, vol. 15, p. 102564, 2019. [Online]. Available: doi: 10.1016/j.rinp.2019.102564
- [92] M. Tourabi et al., "Electrochemical and XPS studies of the corrosion inhibition of carbon steel in hydrochloric acid pickling solutions by 3,5-bis(2-thienylmethyl)-4-amino-1,2,4-triazole," *Corros. Sci.*, vol. 75, pp. 123–133, 2013. [Online]. Available: doi: 10.1016/j.corsci.2013.05.023
- [93] U. M. Eduok, S. A. Umoren, and A. P. Udoh, "Synergistic inhibition effects between leaves and stem extracts of *Sida acuta* and iodide ion for mild steel corrosion in 1 M H<sub>2</sub>SO<sub>4</sub> solutions," *Arabian J. Chem.*, vol. 5, pp. 325–337, 2012.
- [94] B. D. Mert et al., "Experimental and theoretical investigation of 3-amino-1,2,4-triazole-5-thiol as a corrosion inhibitor for carbon steel in HCl medium," *Corros. Sci.*, vol. 53, no. 12, pp. 4265–4272, 2011. [Online]. Available: doi: 10.1016/j.corsci.2011.08.038
- [95] NACE International, "Laboratory Corrosion Testing of Metals in Static Chemical Cleaning Solutions at Temperatures below 93°C (200°F)," TM0193-2016-SG, 2000.
- [96] K. M. Manamela et al., "Adsorptive and DFT studies of some imidazolium based ionic liquids as corrosion inhibitors for zinc in acidic medium," *Int. J. Electrochem. Sci.*, vol. 9, pp. 3029–3046, 2014.
- [97] N. S. Abtan et al., "Unlocking the Power of 4-Acetamidoantipyrine: A Promising Corrosion Inhibitor for Preserving Mild Steel in Harsh Hydrochloric Acid Environments", *Prog Color Colorants Coat.*, vol. 17, pp. 85-96, 2024. [Online]. Available: doi: 10.30509/pccc.2023.167147.1223
- [98] A. K. Singh et al., "Cefacetrile as Corrosion Inhibitor for Mild Steel in Acidic Media," *Int. J. Electrochem. Sci.*, vol. 6, pp. 5689–5700, 2011.
- [99] S. Al-Bghdadi et al., "Benzylidene as Efficient Corrosion Inhibition of Mild Steel in Acidic Solution," *Proceedings*, 2019, p. 27. [Online]. Available: doi: 10.3390/ecsoc-23-06472
- [100] B. S. Mahdi et al., "Gravimetric analysis and quantum chemical assessment of 4-aminoantipyrine derivatives as corrosion inhibitors," *Int. J. Corros. Scale Inhib.*, vol. 11, no. 3, pp. 1191–1213, 2022. [Online]. Available: doi: 10.17675/2305-6894-2022-11-3-17
- [101] A. A. Alamiery, "Study of Corrosion Behavior of N'-(2-(2-oxomethylpyrrol-1-yl) ethyl) piperidine for Mild Steel in the Acid Environment," *Biointerface Res. Appl. Chem.*, vol. 12, pp. 3638–3646, 2022. [Online]. Available: doi: 10.33263/BRIAC123.36383646
- [102] A. Alamiery et al., "Comparative data on corrosion protection of mild steel in HCl using two new thiazoles," *Data Brief*, vol. 40, p. 107838, 2022. [Online]. Available: doi: 10.1016/j.dib.2022.107838
- [103] A. M. Mustafa et al., "Inhibition of mild steel corrosion in hydrochloric acid environment by 1-amino-2-mercapto-5-(4-(pyrrol-1-

- yl)phenyl)-1,3,4-triazole," *S. Afr. J. Chem. Eng.*, vol. 39, pp. 42–51, 2022. [Online]. Available: doi: 10.1016/j.sajce.2021.11.009
- [104] D. M. Jamil et al., "Carbonylthiazole corrosion inhibitor: as an experimentally model and DFT theory," *J. Eng. Appl. Sci.*, vol. 13, pp. 3952–3959, 2018. [Online]. Available: doi: 10.3923/JEASCI.2018.3952.3959
- [105] A. Alobaidy et al., "Eco-friendly corrosion inhibitor: experimental studies on the corrosion inhibition performance of creatinine for mild steel in HCl complemented with quantum chemical calculations," *Int. J. Electrochem. Sci.*, vol. 10, pp. 3961–3972, 2015. [Online]. Available: doi: 10.1016/S1452-3981(23)06594-X
- [106] A. Al-Amiery et al., "Synthesis, characterization and gravimetric studies of novel triazole-based compound," *Int. J. LowCarbon Technol.*, vol. 15, no. 2, pp. 164–170, 2020. [Online]. Available: doi: 10.1093/ijlct/ctz067
- [107] S. Junaedi et al., "Synthesis and characterization of novel corrosion inhibitor derived from oleic acid: 2-Amino-5- Oleyl 1,3,4-Thiadiazol (AOT)," *Int. J. Electrochem. Sci.*, vol. 7, pp. 3543–3554, 2012. [Online]. Available: doi: 10.1016/S1452-3981(23)13976-9
- [108] H. Ibraheem et al., "4-Thiadiazole: The Biological Activities," *Sys. Rev. Pharm.*, vol. 9, no. 1, pp. 36–40, 2018. [Online]. Available: doi: 10.5530/srp.2018.1.7
- [109] A. Al-Amiery et al., "Green Antioxidants: Synthesis and Scavenging Activity of Coumarin Thiadiazoles as Potential Antioxidants Complemented by Molecular Modeling Studies," *Free Radicals Antioxid.*, vol. 6, no. 2, pp. 173–177, 2016. [Online]. Available: doi: 10.5530/fra.2016.2.7
- [110] A. Al-Amiery et al., "Synthesis, Antimicrobial And Antioxidant Activities of 5-((2-Oxo-2h-Chromen-7- Yloxy)Methyl)-1,3,4-Thiadiazol-2(3h)One Derived From Umbelliferone," *Chem. Nat. Compd.*, vol. 48, pp. 950–954, 2013. [Online]. Available: doi: 10.1007/s10600-013-0436-0
- [111] I. Annon et al., "Corrosion inhibition of mild steel in hydrochloric acid environment using thiadiazole derivative: Weight loss, thermodynamics, adsorption and computational investigations," *S. Afr. J. Chem. Eng.*, vol. 41, pp. 244–252, 2022. [Online]. Available: doi: 10.1016/j.sajce.2022.06.011
- [112] H. S. Aljibori et al., "Recent progresses in thiadiazole derivatives as corrosion inhibitors in hydrochloric acid solution," *Int. J. Corros. Scale Inhib.*, vol. 12, no. 3, pp. 842–866, 2023. [Online]. Available: doi: 10.17675/2305-6894-2023-12-3-3
- [113] L. M. Shaker et al., "Corrosion in solar cells: challenges and solutions for enhanced performance and durability," *J. Opt.*, 2023. [Online]. Available: doi: 10.1007/s12596-023-01277-9
- [114] E. A. Noor and A. H. Al-Moubaraki, "Thermodynamic study of metal corrosion and inhibitor adsorption processes in mild steel/1-methyl-4[4'-(X)-styryl pyridinium iodides/hydrochloric acid systems," *Mater. Chem. Phys.*, vol. 110, pp. 145–154, 2008. [Online]. Available: doi: 10.1016/j.matchemphys.2008.01.028
- [115] M. Taha Mohamed et al., "Revolutionizing Corrosion Defense: Unlocking the Power of Expired BCAA", *Prog Color Colorants Coat.*, vol. 17, no. 2, pp. 97-111, 2024. [Online]. Available: doi: 10.30509/pccc.2023.167156.1228
- [116] M. K. Abbass et al., "Evaluation of 2-Dimethylaminopropionamidoantipyrine as a Corrosion Inhibitor for Mild Steel in HCl Solution: A Combined Experimental and Theoretical Study", *Prog Color Colorants Coat.*, vol. 17, no. 1, pp. 1-10, 2024. [Online]. Available: doi: 10.30509/pccc.2023.167081.1197.
- [117] K.Z. Abdulsada et al., "Unleashing the power of polymer surfactants: novel corrosion inhibitors for mild steel in hydrochloric acid," *Int. J. Corros. Scale Inhib.*, vol. 12, no. 4, pp. 2198-2020, 2023. [Online]. Available: doi: 10.17675/2305-6894-2023-12-4-40
- [118] H.S. Aljibori et al., "Advances in corrosion protection coatings: A comprehensive review," *Int. J. Corros. Scale Inhib.*, vol. 12, no. 4, pp. 1476-1520, 2023. [Online]. Available: doi: 10.17675/2305-6894-2023-12-4-6.
- [119] Y.K. Al-Majedy et al., "Exploring chromone derivatives as environmentally friendly corrosion inhibitors for mild steel in acidic environments: A comprehensive experimental and DFT study," *Int. J. Corros. Scale Inhib.*, vol. 12, no. 3, pp. 1028-1051, 2023. [Online]. Available: doi: 10.17675/2305-6894-2023-12-3-14.
- [120] A. Mohammed et al., "Investigation of the Corrosion Inhibition Properties of 4-Cyclohexyl-3-Thiosemicarbazide on Mild Steel in 1 M HCl Solution", *Prog. Color Colorants Coat.*, vol. 16, pp. 347-359, 2023. [Online]. Available: doi: 10.30509/pccc.2023.167126.1212